

# Corrosion resistance of zinc in water

## Introduction

Corrosion rates of zinc in natural fresh water are dependent upon the type and condition of the water. Some of the variables which affect the corrosion rate are as follows:

1. Hard waters are normally less corrosive than soft waters due to the protective calcium and magnesium-based compounds which are deposited on the metal surface as scale.
2. As with other common metals the corrosion rate of zinc increases with aeration of the water. Dissolved oxygen and carbon dioxide both increase the corrosion rate of zinc.
3. Corrosive anion loading (such as chlorides and sulphates) will accelerate related corrosion mechanisms.
4. Agitation or stirring of water leads to increased corrosion but attack is uniform. Under stagnant conditions or conditions of limited oxygen availability attack may be localised in the form of pits.
5. Zinc offers good corrosion resistance in water having a pH near neutral. The corrosion rate is low over the range 6.5-12 but increases rapidly towards the acidic and alkaline sides of this range (see Figure 1). Most neutral potable waters have a pH range from 5.0-8.5.
6. Figure 2 shows that as the temperature of still water rises above approximately 50°C the corrosion rate of zinc increases sharply and reaches a maximum at about 70°C, thereafter the rate decreases rapidly. The increase in corrosion rate followed by a decrease is attributed to a change in the character of the corrosion product. A gelatinous adherent film is formed in the temperature range 20-50°C, a granular flaky or non-adherent film between 50-70°C and a compact dense film above 75°C, which becomes more adherent with a further rise in temperature. At temperatures above 70°C a reversal of polarity can occur in aerated solutions. That is, when the steel substrate is exposed, such as that at a cut edge, it will actually begin to corrode to protect the zinc coating.

As a result of the variable nature of most natural waters due to increases in acid rain and salinity levels, BlueScope only recommends the use of AQUAPLATE® polymer coated steel to contain water. This product consists of a polymer lining which is bonded to a zinc-coated steel substrate. Specific installation design requirements have been made to cover the use of this product and these are contained in [Technical Bulletin TB-3 AQUAPLATE® steel for water tanks](#).


ZINCALUME® steel and COLORBOND® steel should not be used for the containment of water. Refer to [Corrosion Technical Bulletin CTB-16 Immersion](#), for further details.

## Related BlueScope Steel Technical Bulletins


[Technical Bulletin TB-3 AQUAPLATE® steel for water tanks](#)

[Corrosion Technical Bulletin CTB-16 Immersion](#)

**Figure 1: Effect of pH value on the corrosion rate of various metals**

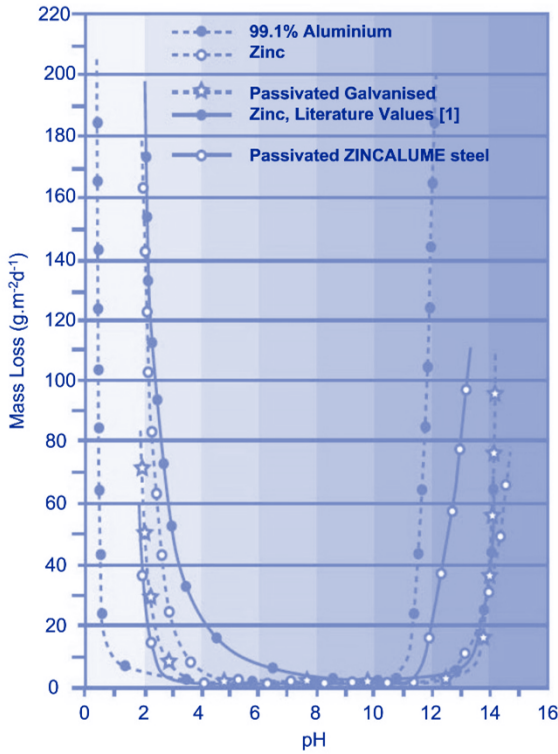

**Figure 2: Effect of water temperature on the corrosion of zinc**

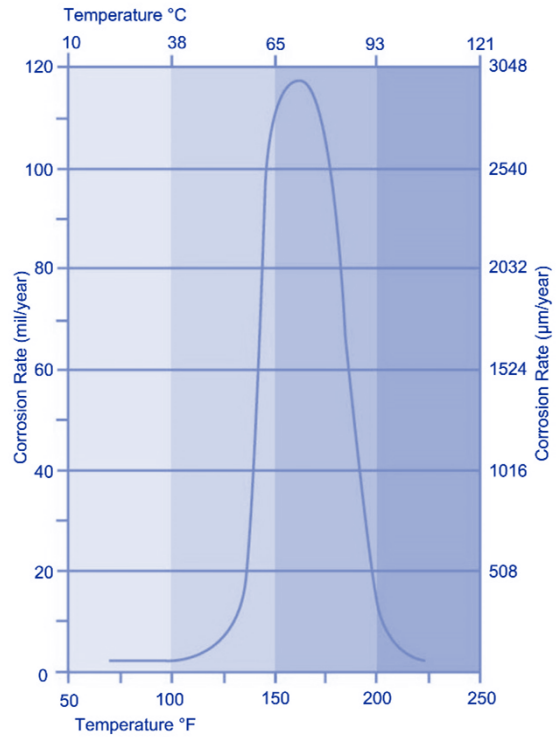

**[steel.com.au](http://steel.com.au)**

To ensure you have the most current information

**1800 800 789**

[steeldirect@bluescopesteel.com](mailto:steeldirect@bluescopesteel.com)

For more information contact Steel Direct



The information and advice contained in this Technical Bulletin ('Bulletin') is of a general nature only and has not been prepared with your specific needs in mind. You should always obtain specialist advice to ensure that the materials, approach and techniques referred to in this Bulletin meet your specific requirements. BlueScope Steel Limited makes no warranty as to the accuracy, completeness or reliability of any estimates, opinions or other information contained in this Bulletin and to the maximum extent permitted by law, BlueScope Steel Limited disclaims all liability and responsibility for any loss or damage, direct or indirect, which may be suffered by any person acting in reliance on anything contained in or omitted from this Bulletin. AQUAPLATE®, COLORBOND® and ZINCALUME®, BlueScope and the BlueScope brand mark are registered trademarks of BlueScope Steel Limited. © 2022 BlueScope Steel Limited ABN 16 000 011 058. All rights reserved.