

Environmental Product Declaration

In accordance with ISO 14025
and EN 15804:2012+A2:2019



ZINCALUME® steel EPD



EPD®
AUSTRALASIA
ENVIRONMENTAL PRODUCT DECLARATION

Programme: **EPD Australasia** | epd-australasia.com

Programme Operator: **EPD Australasia Limited**

EPD Registration number: **S-P-08456**

Version **1.0**

Publication date: **2023-05-30**

Version date: **2023-05-30**

Valid until: **2028-05-30**

Geographical scope: **Australia**

Environmental Product Declaration

ZINCALUME® steel

Programme-Related Information and Verification

| | |
|---|--|
| EPD Owner: | BlueScope Steel Ltd steeldirect@bluescopesteel.com www.bluescope.com Level 11, 120 Collins St, VIC 3000, Australia |
| EPD Produced by: | thinkstep-anz info@thinkstep-anz.com www.thinkstep-anz.com |
| Programme Operator: | EPD Australasia Ltd info@epd-australasia.com www.epd-australasia.com 315a Hardy Street, Nelson 7010, New Zealand |
| Product Category Rules (PCR): | PCR 2019:14 Construction Products, Version 1.11, 2021-02-05 |
| PCR review conducted by: | The Technical Committee of the International EPD® System Chair: Claudia A. Peña Contact: info@environdec.com |
| Independent verification of the declaration and data, according to ISO 14025: | <input type="checkbox"/> EPD process certification <input checked="" type="checkbox"/> EPD verification (external) |
| Third party verifier: |  Rob Rouwette, start2see Pty Ltd Rob.Rouwette@start2see.com.au |
| Verifier approved by: | EPD Australasia Ltd |
| Procedure for follow-up during EPD validity involves third party verifier: | <input type="checkbox"/> Yes <input checked="" type="checkbox"/> No |
| Version History: | v1.0 Initial release. |

General Information

- EPDs within the same product category but from different programmes may not be comparable.
- EPDs of construction products may not be comparable if they do not comply with EN 15804:2012+A2:2019 or if they are produced using different Product Category Rules (PCR).
- BlueScope Steel Limited has sole ownership, liability and responsibility for this EPD.

Woodcroft Neighbourhood Centre

Woodcroft, NSW

Architect: Carter Williamson Architects

Photography: Brett Boardman

Roof made from ZINCALUME® steel



Environmental Product Declaration

ZINCALUME® steel

BlueScope Steel Products

Woodcroft Neighbourhood Centre

Rising from the ashes of its predecessor, which burned down in 2015, the Woodcroft neighbourhood centre sets a new standard in community architecture.

The design relied on steel to achieve the stunning roofline, which connects the proportional volumes of the various interior spaces in a beautiful serpentine line. The roof made from ZINCALUME® steel represents an aesthetic reference to the industrial history of the site.

Woodcroft Neighbourhood Centre

Woodcroft, NSW

Architect: Carter Williamson Architects

Photography: Brett Boardman

Roof made from ZINCALUME® steel



Declared Unit

This EPD provides data for one flat square metre (1 m²) of ZINCALUME® steel manufactured by BlueScope in Australia at certain Base Metal Thicknesses (BMTs) ranging from 0.30 to 1.20 mm.

Key Insights

Benefits of using this EPD 8

This EPD can contribute to the achievement of credits under green building rating schemes. It:

- Is independently verified
- Includes indicators for Green Star and IS Rating

BlueScope's Climate Action 10

Steel and embodied carbon 11

Achieving sustainable outcomes with steel 12

Product Information 16

Product description 16

Product content 17

Scope of the declaration 19

- Cradle-to-gate (A1-A3) with modules C1-C4 and module D
- Includes an extension of the A1-A3 scope to include rollforming up to the rollformer gate

Environmental Performance 22

Results for one flat square metre (1 m²) of ZINCALUME® steel in the following base metal thicknesses (BMTs) where the base metal is the steel:

- 0.30 mm 24
- 0.35 mm 26
- 0.38 mm 28
- 0.40 mm 30
- 0.42 mm 32
- 0.48 mm 34
- 0.50 mm 36
- 0.55 mm 38
- 0.60 mm 40
- 0.70 mm 42
- 0.75 mm 44
- 0.95 mm 46
- 1.00 mm 48
- 1.15 mm 50
- 1.20 mm 52

Note: EN 15804:2012+A1:2013 compliant results are also given in this document to assist comparability across EPDs and support use in tools such as Green Star and IS Rating.

Benefits of using this EPD

This EPD can contribute to the achievement of credit points under Green Star rating tools, the IS Rating Scheme (IS) and other leading green building rating schemes.

Green Star

Green Star registered projects can score points for using products with EPDs. BlueScope's steel products and this EPD may help obtain points in:

- Green Star – Design and As Built v1.3
 - Credit 19A – Life Cycle Assessment
 - Credit 19B.2 – Life Cycle Impacts – Steel
 - Credit 20.1 – Responsible Building Materials
 - Credit 21 – Sustainable Products
- Green Star – Buildings
 - Credits 6 to 9 – Responsible Products (Structure, Envelope, Systems or Finishes)
 - Credit 21 – Upfront Carbon Emissions
 - Credit 26 – Life Cycle Impacts
- Green Star – Communities v1.1
 - Credit 26 – Materials

IS Rating

IS projects can claim points for using products with EPDs. EPD results can also be included in the IS Materials Calculator and may help a project achieve reductions compared to a 'base case' footprint.

BlueScope's steel products and this EPD may help obtain points in:

- IS Design & As Built v1.2
 - Mat-1 Materials Life Cycle Impact Measurement and Reduction
 - Mat-2 Environmentally Labelled Products and Supply Chains
- IS Design & As Built v2.1
 - Rso-6 Materials Life Cycle Impact Measurement and Reduction
 - Rso-7 Sustainability Labelled Products and Supply Chains

BlueScope's products are also included in the Infrastructure Sustainability Council (ISC) ISupply Directory which connects products and services with projects and assets undertaking IS ratings.

This EPD also provides:

- Environmental performance information from cradle to gate (modules A1-A3), with an extension of the A1-A3 scope to include rollforming up to the rollformer gate, plus modules C1-C4 and module D.
- Carbon footprint data for use in Scope 3 carbon footprint calculations of your supply chain
- A wide range of environmental metrics, such as water, energy and waste

For more information on how BlueScope's products can help achieve more sustainable project outcomes contact BlueScope Steel Direct on 1800 800 789.

Take care when comparing

When comparing EPDs it is important to consider:

- EPDs within the same product category but from different programmes or utilising different Product Category Rules (PCRs) may not be comparable.
- The results for EN 15804:2012+A1:2013 compliant EPDs are not comparable with EN 15804:2012+A2:2019 compliant ones, as the methodologies differ. This EPD provides additional results in accordance to EN 15804:2012+A1:2013 to assist comparability across EPDs and support use in rating tools such as Green Star and IS Rating.
- EPDs of construction products from a group of manufacturers (industry-wide EPD) may not be comparable to an EPD of a similar construction product that has been generated by a single manufacturer (product-specific or manufacturer-specific EPD).
- Understanding the detail is important in comparisons. Expert analysis is often required to understand the detail and ensure data is truly comparable, to avoid unintended distortions.
- The best way to compare products and materiality of differences is to place them into the context of a structure across the whole life cycle.

If you need help interpreting the data in this EPD, please contact BlueScope Steel Direct on 1800 800 789.

BlueScope's Climate Action

Steel is an essential material for modern society and a critical enabler of sustainable development. We recognise that steelmaking is emissions-intensive and we are committed to climate action. Our climate strategy outlines our decarbonisation plans, including our goal of net zero greenhouse gas emissions across our operations by 2050¹, dependent on several enablers based around technology, renewable energy and public policy.

We have a promising innovation pipeline including collaborations with Rio Tinto and others, to explore ways to decarbonise iron and steelmaking processes. We believe these projects will help take us to the cutting edge of current technologies and demonstrate our commitment to reduce the embodied carbon of our products.

More information on BlueScope's climate action, can be found on our website: www.bluescope.com/sustainable-steel

OUR PATHWAY

SET A GOAL FOR:

NET ZERO

GHG emissions across our operations by 2050¹

SET TARGETS FOR:

12%

GHG emission intensity reduction by 2030 for our steelmaking activities (based on 2018 levels)

30%

GHG emission intensity reduction by 2030 for our non-steelmaking activities² (based on 2018 levels)

1. Our net zero goal covers BlueScope's Scope 1 and 2 GHG emissions. Achieving the 2050 net zero goal is highly dependent on several enablers, including commerciality of emerging and breakthrough technologies, the availability of affordable and reliable renewable energy and hydrogen, availability of quality raw materials, and appropriate policy settings.

2. The Non-Steelmaking Target applies to our midstream activities that include our cold rolled, metal coating and painting lines and long and hollow products. It excludes our downstream activities.

3. Pickin J et al., National Waste Report 2020, Prepared for the Department of Agriculture, Water and the Environment; 2020, p. 39.

4. Refers to the carbon emissions, or emissions of greenhouse gases, associated with materials throughout the life cycle of a building or infrastructure, not to the carbon content in the metal alloy.

5. www.worldsteel.org/about-steel/steel-facts.html

6. www.iea.org/reports/iron-and-steel-technology-roadmap



Steel and Embodied Carbon

Steel is one of the most recycled materials in the world, with the inherent value of scrap driving its recovery. In Australia, this is evidenced by a recycling rate for metals of 90%³. The recyclability of steel is enabled by its magnetic properties, which mean that it can be easily separated for recycling and is less likely to end up in landfill.

The recycled content in a steel product can have a significant effect on embodied carbon. While specifying high levels of recycled content can be an effective way of minimising the embodied carbon⁴ of many materials, especially those likely to be disposed of at end of life, recycled content is not necessarily a useful metric for steel in the context of reduction of carbon emissions by the steel sector. This is because despite being one of the most recycled materials in the world⁵, there is not enough steel scrap available to meet the growing global demand for steel⁶.

Specification of 'secondary' steel or steel products with higher levels of recycled content as a means of reducing embodied carbon, is unlikely to cause more steel to be recycled. Rather, doing so may shift the environmental burden around the value chain, and in fact increase the burden, as scrap and the final product may be transported around the globe unnecessarily.

While global demand for scrap continues to outstrip supply, the development and deployment of new low GHG emissions technologies for 'primary' steel production (using raw material inputs such as iron ore and metallurgical coal) while increasing the role of 'secondary' steelmaking (principally using scrap steel), will be key to reducing carbon emissions in the steel sector.



BlueScope is a founding member of ResponsibleSteel™, the steel industry's first global multi-stakeholder standard and certification program. It has been designed to ensure customers, stakeholders and consumers can be confident that the steel they use has been sourced and produced responsibly.

Initiatives, such as ResponsibleSteel™, are incorporating new methodologies to ensure that the carbon emissions of steel products are calculated on a like-for-like basis, irrespective of the input materials used and the steel production technology.

Embodied carbon and climate transition in a hard-to-abate sector

There is growing recognition from research and standard setting organisations that the percentage of recycled content in steel is not a good proxy for climate transition for the steel sector.

New methodologies, tools and guidance are being developed by organisations such as ResponsibleSteel™, to enable steel companies to set targets that align with science-based decarbonisation pathways and consider the unique context of the sector.

BlueScope is a participant in the Expert Advisory Group convened by the Science Based Targets initiative (SBTi) for the development of science-based target setting methodologies, tools and guidance in the steel sector to help meet the 1.5 °C goal of the Paris Agreement.

These initiatives build on the work of the Net Zero Steel Pathway Methodology Project (NZSPMP), which developed recommendations to identify and recognise low carbon emissions steelmaking, irrespective of the proportion of scrap or iron ore used as the primary input material. This approach would enable users to identify and reward reductions in embodied carbon and efficiencies in manufacturing practices for the steel sector, rather than simply identifying products that use more or less scrap steel, creating the basis for downstream users of steel to contribute to the achievement of the Paris Agreement through their steel specifying and purchasing decisions, and to recognise responsible steelmakers for their own commitment.

More information: www.sciencebasedtargets.org/sectors/steel and www.netzerosteelproject.com

Achieving Sustainable Outcomes with Steel

Steel is central to a circular economy – one where resources and materials are kept in use for as long as possible and then repaired, returned or recycled. Steel can be infinitely recycled and is 100% recyclable without loss of quality.

Design considerations

Life cycle thinking. A focus on design is important to minimise the whole of life impact of any construction project. Steel is a strong, durable and versatile material. It lends itself well to structures that are designed for long life, resilience and flexibility to accommodate multiple future reuse options without reinvestment in structural alteration and refurbishment. Steel also supports designs where end of life considerations are key e.g. designing for disassembly and reuse.

Dematerialisation. BlueScope manufactures a range of standard and high strength steel grades in plate and coil form. High strength steel grades enhance the strength to weight performance in structural steel applications when the design is governed by strength; by maximising the strength grade, a reduced volume of steel would be required in these applications, e.g. columns and primary members. This in turn can result in embodied carbon savings relative to a reference building design that utilises standard steel grades.

Specification considerations

ResponsibleSteel™. ResponsibleSteel™ is the steel industry's first global multi-stakeholder standard and certification initiative. The ResponsibleSteel™ Standard covers a wide range of sustainability topics, including Climate Change and Greenhouse Gas Emissions, Biodiversity, Water Stewardship and Human Rights. Specifying steel from a ResponsibleSteel™ certified site supports steel manufacturers such as BlueScope who are committed to climate action and sustainability. It also supports those downstream to manage ESG (Environmental, Social and Governance) risks in the steel supply chain.

More information: www.responsiblesteel.org

EPDs and ecolabels. EPDs and ecolabels demonstrate a manufacturer's commitment to product transparency and stewardship. EPDs and ecolabels provide key sustainability information to support decision-making and the achievement of more sustainable outcomes.

Further information on the sustainability credentials of BlueScope's products: www.steel.com.au

Manufacturer commitments and investment. Understand the commitments manufacturers have made to sustainability and climate change action and consider their investment in Research & Development activities.

More information on BlueScope's commitments and activities can be found in our Climate Action Report and Sustainability Report: www.bluescope.com/sustainable-steel/reports/



Montoro Cellar Door

Orange, NSW

Architect: Source Architects

Photography: Tom Ferguson

Roof made from ZINCALUME® steel

Contributing to a Sustainable Future

BlueScope has a long-standing commitment to developing innovative, responsible products and services. You can design and specify with confidence, knowing that ZINCALUME® steel is created with durability, performance, compliance and sustainability top of mind.

Steel and the Circular Economy

Steel is strong, durable, and versatile and its inherent properties allow it to be recycled without loss of quality over and over again. In some cases, it can be reused without reprocessing, again saving on energy and resource use.

To help support a more sustainable 'circular economy', the steel manufactured by BlueScope in Australia incorporates pre- and post-consumer recycled content⁷. Steel is 100% recyclable and its magnetic properties mean that it can be easily separated for recycling and is less likely to end up in landfill.

Durable and Resilient

ZINCALUME® steel is durable and resilient to Australia's harsh climate, with BlueScope's industry-leading metallic coating, incorporating Activate® technology, to provide enhanced corrosion resistance. Its long life can help conserve resources and energy that may otherwise be invested in products with shorter life spans.



Warranty Confidence

When you specify, purchase or install ZINCALUME® steel you are also benefiting from the support of BlueScope, one of Australia's largest manufacturers.

ZINCALUME® steel is known for its durability, and is backed by BlueScope. BlueScope offers a variety of warranties subject to application and eligibility criteria⁸.



Certification of Port Kembla Steelworks

BlueScope's Port Kembla Steelworks is certified to the ResponsibleSteel™ Standard version 1.1. Australia's largest steel production facility has an annual production capacity of approximately 3 million tonnes of crude steel.

It manufactures slab, hot rolled coil and plate products. Branded products such as ZINCALUME® steel, COLORBOND® steel, TRUECORE® steel and XLERPLATE® steel are manufactured from steel produced at the Port Kembla Steelworks.

⁷ Across the range of steel products manufactured by BlueScope in Australia, the average recycled content (according to recycled content categories defined in ISO 14021:2016) in the steel is 17.4%, which includes pre- and post-consumer recycled materials. Scrap and iron-bearing materials generated and reclaimed from BlueScope's steelmaking, coating and painting operations represent an additional 6.8% recovered content, which is not reported as recycled content. Scrap from rollforming and fabrication processes are included as pre-consumer recycled content. The figures provided represent our best estimate at the time of publication. For current recycled content figures please contact BlueScope Steel Direct on 1800 800 789.

⁸ Warranties subject to exclusions, application, and eligibility criteria. For full terms and conditions visit www.bluescopesteel.com.au/warranties.

Environmental Product Declaration

ZINCALUME® steel

Declared Unit

This EPD is valid for one flat square metre (1 m²) of ZINCALUME® steel manufactured by BlueScope in Australia.



Product Description

ZINCALUME® steel incorporating Activate® technology is an aluminium, zinc, and magnesium alloy coated steel product.

It is typically formed into roofing and walling, garage doors, structural sections, or other general manufactured articles. It suits a wide range of building designs including a variety of commercial and industrial projects as well as rural sheds. It can also be used as an iconic design feature in residential applications.

This EPD sets out information on the average ZINCALUME® steel product⁹ manufactured by BlueScope in Australia, in the base metal thicknesses (BMTs) presented in the table below.

The ZINCALUME® steel products represented in this EPD consist of a low carbon¹⁰ steel substrate that is coated with a metallic coating incorporating BlueScope's Activate® technology (hot dipped aluminium, zinc, and magnesium alloy AM125 coating) to provide enhanced corrosion resistance.

The metallic coated base steel (G2N, G250, G300, G450, G500 or G550 strength grade), conforms to AS 1397:2021: *Continuous hot-dip metallic coated steel sheet and strip - Coatings of zinc and zinc alloyed with aluminium and magnesium*.

| Product | Metallic Coating | Base Metal Thickness (BMT) | Product mass (kg/m ² flat product) |
|------------------|------------------|----------------------------|---|
| ZINCALUME® steel | AM125 | 0.30 mm | 2.49 |
| | | 0.35 mm | 2.88 |
| | | 0.38 mm | 3.12 |
| | | 0.40 mm | 3.27 |
| | | 0.42 mm | 3.43 |
| | | 0.48 mm | 3.90 |
| | | 0.50 mm | 4.06 |
| | | 0.55 mm | 4.45 |
| | | 0.60 mm | 4.84 |
| | | 0.70 mm | 5.63 |
| | | 0.75 mm | 6.02 |
| | | 0.95 mm | 7.59 |
| | | 1.00 mm | 7.98 |
| 1.15 mm | 9.16 | | |
| 1.20 mm | 9.55 | | |

Manufacturing Process

In Australia, BlueScope manufactures steel from raw and recycled materials using an 'integrated steelmaking' method. This involves the use of iron ore, coal, steel scrap, fluxes (limestone and dolomite) and alloying materials to produce steel slab via the major processes of sintering, coke making, Blast Furnace/Basic Oxygen Furnace (BF-BOF) steelmaking and continuous slab casting, prior to hot rolling into hot rolled coil steel.

The hot rolled coil is then cold reduced. Cold reduction involves pickling (acid cleaning) the coil, followed by cold rolling, where the steel coil is compressed and elongated through rolls to reduce its thickness and increase the strength of the steel. Following cold reduction, the coil moves through a continuous hot-dipped metal coating line. At the metal coating line the steel is annealed to the required strength, metallic coated for corrosion resistance, and then a chemical surface treatment and resin coating are applied to help protect the product through transportation, storage and downstream processing. The coil is then packaged ready for shipment to customers for processing.

Downstream Processing

ZINCALUME® steel is supplied by BlueScope to downstream processors in coil form. These coils are uncoiled and formed into roofing and walling profiles, structural sections and other general manufactured articles. The finished products are delivered to construction sites for installation.

To provide indicative results for the final formed product up to the rollforming gate, data has been obtained from selected sites of several rollformers based in Australia, including Lysaght (all sites), Metroll (Perth, Albany and Bunbury sites) and Steeline (Hunter site). These results are presented as 'A1-A3 incl. rollforming' in the Results section. The indicative rollforming results represent an average of the data collected across the range of steel products formed from the surveyed sites¹¹. These results may not be representative of the final formed product from any particular rollforming operation, company or site. Actual results will vary depending on a range of factors specific to the particular operations of the downstream processors.

Product Content

The average composition¹² of one flat square metre (1 m²) of ZINCALUME® steel is:

| Product composition | | Mass (kg) | Recycled material (pre- and post-consumer) |
|--------------------------|--------------|---------------------------------|---|
| Steel Substrate | Carbon Steel | 2.36 (0.30 mm) – 9.42 (1.20 mm) | 17.4% (average recycled content in the steel manufactured by BlueScope in Australia) ¹³ |
| | Aluminium | 0.061–0.074 | - |
| Metallic Coating (AM125) | Magnesium | 0.001–0.004 | - |
| | Silicon | 0.001–0.003 | - |
| | Zinc | 0.049–0.066 | - |
| Surface treatment | Passivation | <0.002 | - |
| | Resin | ≤0.002 | - |

| Packaging Materials | Mass (kg) | Packaging (as % of product mass) |
|---------------------|-----------|----------------------------------|
| Steel | 0.012 | 0.09%-0.35% |
| Plastic | 0.002 | 0.02%-0.06% |
| Cardboard | 0.001 | 0.01%-0.03% |
| Timber | 0.007 | 0.06%-0.20% |

ZINCALUME® steel is compliant with the European REACH regulation¹⁴. For safe use and maintenance information, refer to the product Safety Data Sheet (SDS) at www.steel.com.au/library.

What is an SDS?

A Safety Data Sheet (SDS) is a document that describes the chemical and physical properties of a product or material and provides safe handling and use information.

Industry Classification

| Product | Classification | Code | Category |
|------------------|----------------|-------|---|
| ZINCALUME® steel | UN CPC | 41231 | Flat-rolled products of non-alloy steel, clad, plated, coated or otherwise further worked |
| | ANZSIC | 2110 | Iron Smelting and Steel Manufacturing |

11. The indicative rollforming results provided are an average and variability among different products, operations, companies and sites is expected. Results are based on rollforming data corresponding to a 12 month period, which varied by rollformer (ranging from July 2018 to June 2021). Some of this data has been obtained from third parties. BlueScope does not accept any responsibility for the accuracy, completeness or reliability of data provided by third parties.

12. The product composition provided is an average and variability among individual products is expected. Please note that we are constantly working to improve our products and changes to their composition may occur over time. If clarification on a particular product is needed please contact BlueScope Steel Direct on 1800 800 789.


13. Across the range of steel products manufactured by BlueScope in Australia, the average recycled content (according to recycled content categories defined in ISO 14021:2016) in the steel is 17.4%, which includes pre- and post-consumer recycled materials. Scrap and iron-bearing materials generated and reclaimed from BlueScope's steelmaking, coating and painting operations represent an additional 6.8% recovered content, which is not reported as recycled content. Scrap from rollforming and fabrication processes are included as pre-consumer recycled content. The figures provided represent our best estimate at the time of publication. For current recycled content figures please contact BlueScope Steel Direct on 1800 800 789.

14. Regulation (EC) No. 1907/2006 of the European Parliament and of the Council of 18 December 2006 on the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH).

9. Refer to the ZINCALUME® steel datasheets at www.steel.com.au

10. The term 'low carbon steel' refers to the carbon content in the metal alloy (which is typically less than 0.3% carbon content), and not to the carbon dioxide (CO₂) emissions associated with the product.

ZINCALUME® steel Manufacturing and Processing in Australia

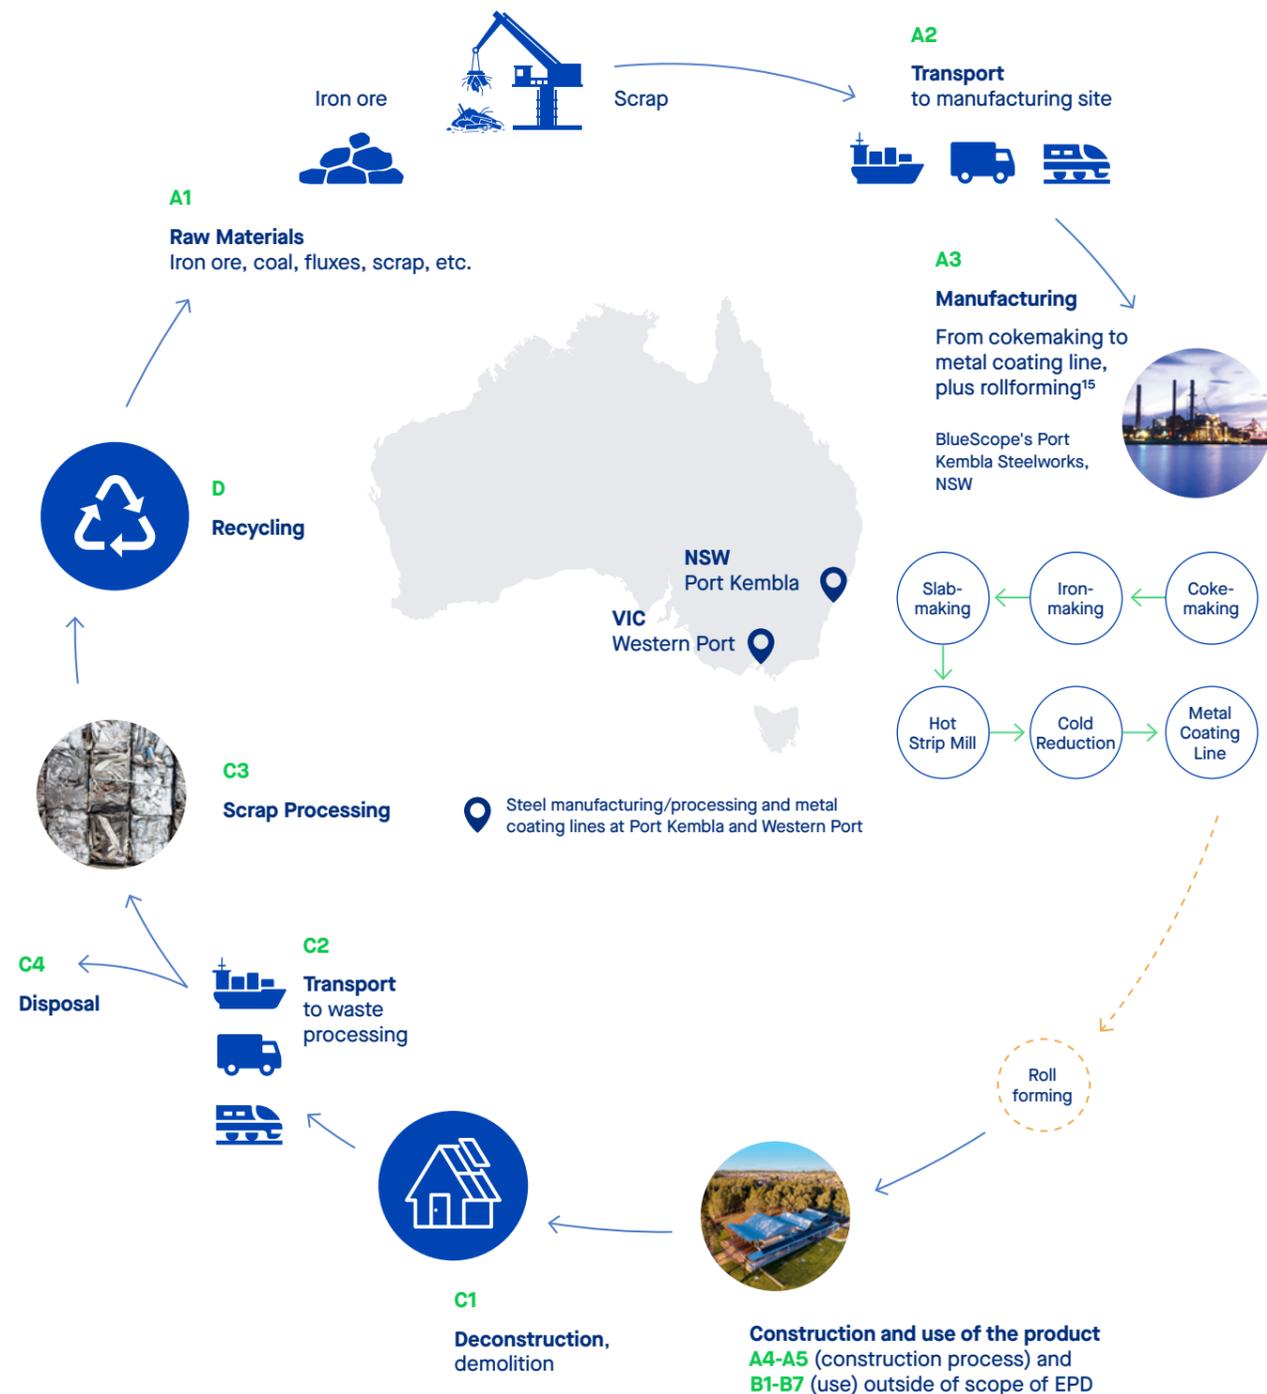

Scope of Declaration

This declaration is for one flat square metre (1 m²) of ZINCALUME® steel manufactured by BlueScope in Australia¹⁶. The scope of this declaration is from cradle to gate (modules A1-A3), with modules C1-C4 and module D. It includes an extension of the modules A1-A3 to include rollforming up to the rollformer gate¹⁷.

Modules A4-A5 (construction process) and B1-B7 (use) have not been included due to the inability to predict how the material will be used following manufacture.

The system boundary applied in this study extends from mining of raw materials such as iron ore and coal; transport to and within the manufacturing site; coke, sinter, iron and steel manufacture; ancillary service operations; hot rolling of steel products, cold reduction, metallic coating and packaging for dispatch to direct customers at the exit gate of the manufacturing site.

The system boundary has been extended to include transport to the rollforming site, rollforming operations and packaging for dispatch to rollformers' customers at the exit gate of the rollforming site, presented as 'A1-A3 incl. rollforming' in the Results section.

The system boundary also includes manufacture of other required input materials, transport between processing operations, the production of external services such as electricity, natural gas and water, and the production of co-product materials within the steelmaking process, which have been removed by the use of allocation techniques. Wastes and emissions to air, land and water are also included, as are modules C1-C4 (end of life stage), and module D (reuse, recovery and/or recycling potential).

| Modules | Product stage | | | Construction process stage | | Use stage | | | | | | End of life stage | | | Benefits and loads beyond the system boundary | | |
|-----------------------------|---------------------|-----------|---------------|----------------------------|-----------------------------|-----------|-------------|--------|-------------|---------------|------------------------|-----------------------|-----------------------------|-----------|---|------------------|----------|
| | Raw material supply | Transport | Manufacturing | Transport | Construction / installation | Use | Maintenance | Repair | Replacement | Refurbishment | Operational energy use | Operational water use | De-construction, demolition | Transport | | Waste processing | Disposal |
| Modules declared | X | X | X | ND | ND | ND | ND | ND | ND | ND | ND | ND | X | X | X | X | X |
| Geography | AU | AU | AU | - | - | - | - | - | - | - | - | - | AU | AU | AU | AU | GLO |
| Specific data | >90% | | | - | - | - | - | - | - | - | - | - | - | - | - | - | - |
| Variation - products | <10% | | | - | - | - | - | - | - | - | - | - | - | - | - | - | - |
| Variation - sites | <10% | | | - | - | - | - | - | - | - | - | - | - | - | - | - | - |

X = Module declared; ND = Not declared (such a declaration shall not be regarded as an indicator of a zero result).

16. As described in the Product Description on page 16.

17. To provide indicative results for the final formed product up to the rollforming gate, data has been obtained from selected sites of several rollformers based in Australia. Results are based on rollforming data corresponding to a 12 month period, which varied by rollformer (ranging from July 2018 to June 2021). The results represent an average of the data collected across the range of steel products formed from the surveyed sites. These results may not be representative of the final formed product from the rollforming operations of other companies or sites. Variability among different products, operations, companies and sites is expected. Actual results will vary depending on a range of factors specific to the particular operations of the downstream processors. Some of this data has been obtained from third parties. BlueScope does not accept any responsibility for the accuracy, completeness or reliability of data provided by third parties.

Life Cycle Assessment (LCA) Methodology

This EPD has been produced in conformance with the requirements of PCR 2019:14 v1.11 Construction Products, the Instructions of the Australasian EPD Programme v3.0 and the International EPD® System General Programme Instructions (GPI) v3.01.

Primary data

This study focuses on the further processing of steel beyond hot rolling to produce ZINCALUME® steel. Upstream hot rolled steel manufacturing data for low carbon¹⁸ Hot Rolled Coil used in this study was obtained from v2.0 of the EPD for Steel – Hot Rolled Coil (S-P-00557).

Primary data were collected for all relevant BlueScope manufacturing sites in Australia, for all inputs and outputs in the production stage (A1-A3). This study is based on an annual average for the time period July 2018 to June 2019. All direct emissions data were procured from the average results reported to the National Pollution Inventory over the 3-year period 2016 to 2019.

To provide indicative results for the final formed product up to the rollforming gate, primary data for rollforming were collected from selected sites of several rollformers based in Australia, including Lysaght (all sites), Metroll (Perth, Albany and Bunbury sites) and Steeline (Hunter sites). The data was collected across a 12 month period ranging from July 2018 to June 2021 for each site.

Secondary data

The secondary data used were procured from the GaBi Life Cycle Inventory Database 2022¹⁹. Most datasets used have a reference year between 2018 and 2021 and all fall within the 10-year limit allowable for generic data under EN 15804.

For the modelling for BlueScope's manufacturing sites, the electricity supply was based on GaBi's state-specific 1kV-60kV grid mix datasets for NSW and VIC as relevant to each BlueScope manufacturing site.

The 2019 1kV-60kV NSW grid mix dataset is highly reliant on hard coal (77%), with imports from VIC (6.5%) and QLD (5.6%), and generation from hydro (4.1%), natural gas (3.3%), wind (2.5%) and photovoltaics (0.74%). The emission factor for the 2019 1kV-60kV NSW grid for the GWP-GHG indicator is 0.987 kg CO₂-eq/kWh (GaBi database 2022).

The 2019 1kV-60kV VIC grid mix dataset is highly reliant on lignite (80%), with generation from hydro (6.3%), wind (6.2%), and natural gas (3.2%), and imports from TAS (2.4%), NSW (1.1%) and SA (0.68%). The emission factor for the 2019 1kV-60kV VIC grid for the GWP-GHG indicator is 1.13 kg CO₂-eq/kWh (GaBi database 2022).

For the modelling for rollforming operations, GaBi state-specific grid mix datasets were used to create a production-weighted average grid mix, based on BlueScope's transport data to rollformers in different States, resulting in an emission factor for the GWP-GHG indicator of 0.942 kg CO₂-eq/kWh.

Water use in relation to BlueScope's manufacturing sites was modelled using the specific watershed scarcity data for each BlueScope manufacturing site. For the rollforming operations, water use was modelled using the generic Australian water scarcity data for rollforming.

Cut off criteria

All relevant and available data were collected. While cut-off criteria according to the Product Category Rules (PCR) section 4.4 were employed, much of the data which would have fallen within that scope were included where available, resulting in a data set which is robust and captures all significant contributors to the LCA results. Inputs knowingly excluded are the transport and packaging of minor inputs, such as lubricants and greases, which are used in very small quantities.

Personnel is excluded as per section 4.3.1 in the PCR (EPD International, 2021). thinkstep-anz consistently excludes environmental impacts from infrastructure, construction, production equipment, and tools that are not directly consumed in the production process ('capital goods'). This is because high-quality infrastructure-related data isn't always available and there is no clear cut-off for what to include. For this reason, capital goods data may be applied to LCA studies inconsistently and could lead to reduced consistency and comparability of EPDs.

Allocation

For the modelling for BlueScope's manufacturing sites, where subdivision of processes was not possible, allocation was carried out using the most relevant physical quantity, predominantly the mass of throughput (e.g. steel coil) or surface area of the coil (e.g. surface coatings). Economic allocation was not used in this study. No use of system expansion was made (excepting Module D).

End of life

The modelling for Module C1 (deconstruction, demolition) was based on the use of a 100 kW construction excavator (fuel consumption of 0.172 kg diesel per tonne steel). The modelling for Module C2 (transport) assumed 50 km transport by truck to a waste processing facility or landfill.

The recycling scenario was based on the National Waste Report 2020²⁰, which indicates that the average metals recycling rate in Australia is 90%. This is considered to be a conservative estimate for flat steel construction products but was used in the absence of verified higher recycling rates.

End of life allocation follows the requirements of EN 15804:2012+A2:2019 section 6.4.3.3 and generally follows the polluter pays principle. Any open scrap inputs into manufacturing remain unconnected, and so are treated as 'burden free'. At the end of life of a product, scrap is collected for recycling and is thus available to produce a recycling credit within Module D. A credit for net scrap is given in Module D based on the base metal used in the product.

Key assumptions and qualifications:

- Accuracy of data measurement falls within normal industrial weighing systems accuracy limits of +/-5%.
- Transport and packaging of minor materials is insignificant to the overall impacts.
- Nominally identical products are produced on a combination of production lines in parallel, and therefore the impacts of each product are a weighted average of the various production lines. The impact of any differences in the composition of the products, with the exception of any change in base metal thickness (BMT), is insignificant on the outcomes of the LCA.
- Proprietary chemicals and resins can be sufficiently modelled using guidance from Safety Data Sheets and conservative assumptions on that basis.
- Upstream data taken from the GaBi LCA database reflects average or generic production and therefore does not correspond to BlueScope's actual suppliers.
- Rollforming data has been obtained from selected sites of several rollformers based in Australia. Some of this data has been obtained from third parties. BlueScope does not accept any responsibility for the accuracy, completeness or reliability of data provided by third parties. The indicative rollforming results represent an average of the data collected across the range of steel products formed from the surveyed sites. The rollforming results may not be representative of the final formed product from any particular rollforming operation, company or site. Variability among different products, operations, companies and sites is expected. Actual results will vary depending on a range of factors specific to the particular operations of the downstream processors.
- The Module D recovery stage assumes that resin coatings are incinerated and metal coatings are lost as slag during the steel recycling process. This is a conservative assumption for metal coatings as they are likely to make up part of future steel alloys.

18. The term 'low carbon' steel refers to the carbon content in the metal alloy (which is typically less than 0.3% carbon content), and not to the carbon dioxide (CO₂) emissions associated with the product.

19. Sphera, GaBi LCA Database Documentation, 2022, <https://www.gabi-software.com/support/gabi/gabi-database-2022-lci-documentation/>

20. Pickin J et al., National Waste Report 2020, Prepared for the Department of Agriculture, Water and the Environment, 2020, p.39.

Environmental Product Declaration

ZINCALUME® steel

Environmental Performance

The environmental impact indicators included in this EPD are described in the table below. All the result tables from this point will contain the abbreviations only. All results reported in MJ are in net calorific value.

| Indicator | Abbreviation | Units | Characterisation Method |
|--|-----------------------|-----------------------------------|-----------------------------------|
| Core Environmental Impact indicators, in accordance to EN 15804:2012+A2:2019 | | | |
| Climate change – total | GWP-total | kg CO ₂ -eq. | EF3.0 (PEF) |
| Climate change – fossil | GWP-fossil | kg CO ₂ -eq. | EF3.0 (PEF) |
| Climate change – biogenic | GWP-biogenic | kg CO ₂ -eq. | EF3.0 (PEF) |
| Climate change – land use and land use change | GWP-luluc | kg CO ₂ -eq. | EF3.0 (PEF) |
| Ozone depletion | ODP | kg CFC-11-eq. | WMO 2014 |
| Acidification | AP | mol H ⁺ -eq. | Accumulated Exceedance |
| Eutrophication aquatic freshwater | EP-freshwater | kg P-eq. | EUTREND model (ReCiPe) |
| Eutrophication aquatic marine | EP-marine | kg N-eq. | EUTREND model (ReCiPe) |
| Eutrophication terrestrial | EP-terrestrial | mol N-eq. | Accumulated Exceedance |
| Photochemical ozone formation | POCP | kg NMVOC-eq. | LOTOS-EUROS |
| Depletion of abiotic resources – minerals and metals | ADP-minerals & metals | kg Sb-eq. | CML 2002a |
| Depletion of abiotic resources – fossil fuels | ADP-fossil | MJ | CML 2002a |
| Water depletion potential | WDP | m ³ world-eq. deprived | AWARE |
| Additional Environmental Impact indicators, in accordance to EN 15804:2012+A2:2019 | | | |
| Climate change | GWP-GHG | kg CO ₂ -eq. | IPCC 2013 (AR5) |
| Particulate Matter emissions | PM | Disease incidence | SETAC-UNEP, Fantke et al. 2016 |
| Ionising radiation – human health | IRP | kBq U-235-eq. | Human Health Effect model |
| Eco-toxicity – freshwater | ETP-fw | CTUe | Modified USEtox model from EC-JRC |
| Human toxicity potential – cancer effects | HTP-c | CTUh | Modified USEtox model from EC-JRC |
| Human toxicity potential – non-cancer effects | HTP-nc | CTUh | Modified USEtox model from EC-JRC |
| Land use related impacts / soil quality | SQP | dimensionless | Soil quality index (LANCA®) |
| Resource use parameters | | | |
| Use of renewable primary energy excluding renewable primary energy resources used as raw materials | PERE | MJ | n/a |
| Use of renewable primary energy resources used as raw materials | PERM | MJ | n/a |
| Total use of renewable primary energy resources | PERT | MJ | n/a |
| Use of non-renewable primary energy excluding non-renewable primary energy resources used as raw materials | PENRE | MJ | n/a |
| Use of non-renewable primary energy resources used as raw materials | PENRM | MJ | n/a |
| Total use of non-renewable primary energy resources | PENRT | MJ | n/a |
| Use of secondary material | SM | kg | n/a |
| Use of renewable secondary fuels | RSF | MJ | n/a |
| Use of non-renewable secondary fuels | NRSF | MJ | n/a |
| Net use of fresh water | FW | m ³ | n/a |

| Waste Categories and Output Flows | | | |
|---|-----------|---------------------------------------|----------------------------|
| Hazardous waste disposed | HWD | kg | n/a |
| Non-hazardous waste disposed | NHWD | kg | n/a |
| Radioactive waste disposed | RWD | kg | n/a |
| Components for re-use | CRU | kg | n/a |
| Materials for recycling | MFR | kg | n/a |
| Materials for energy recovery | MER | kg | n/a |
| Exported energy – electrical | EEE | MJ | n/a |
| Exported energy – thermal | EET | MJ | n/a |
| Additional Environmental Impact indicators, in accordance to EN 15804:2012+A1:2013 | | | |
| Global warming potential | GWP | kg CO ₂ -eq. | IPCC 2007 (AR4) |
| Ozone depletion potential | ODP | kg CFC-11-eq. | WMO 2003 |
| Acidification potential | AP | kg SO ₂ -eq. | CML 2002b |
| Eutrophication potential | EP | kg PO ₄ ³⁻ -eq. | CML 2002b |
| Photochemical ozone creation potential | POCP | kg C ₂ H ₄ -eq. | CML 2002b |
| Abiotic depletion potential for non-fossil resources | ADPE | kg Sb-eq. | CML 2002b |
| Abiotic depletion potential for fossil resources | ADPF | MJ | CML 2002b |
| Additional Green Star v1.3 indicators | | | |
| Human Toxicity – cancer effects | HTc - GS | CTUh | USEtox |
| Human Toxicity - non-cancer effects | HTnc - GS | CTUh | USEtox |
| Land use | LU - GS | kg C deficit-eq. | Soil Organic Matter method |
| Resource depletion – water | RDW - GS | m ³ -eq. | Water Stress Indicator |
| Ionising radiation | IR – GS | kBq U235-eq. | Human Health Effect model |
| Particulate matter | PM - GS | kg PM2.5-eq. | RiskPoll |

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.30mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 2.49 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 8.40 | 8.66 | 0.00155 | 0.0118 | 0.110 | 0.0121 | -2.80 |
| GWP-fossil | kg CO ₂ -eq. | 8.40 | 8.73 | 0.00155 | 0.0118 | 0.109 | 0.0120 | -2.80 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00229 | -0.0667 | 1.54E-07 | 3.93E-06 | 1.22E-04 | 2.37E-05 | 0.00167 |
| GWP-luluc | kg CO ₂ -eq. | 3.84E-04 | 6.86E-04 | 1.13E-08 | 1.27E-07 | 4.20E-06 | 7.23E-06 | -5.61E-05 |
| ODP | kg CFC-11-eq. | 4.96E-12 | 5.49E-12 | 1.23E-16 | 1.18E-15 | 4.87E-13 | 1.58E-14 | 4.80E-14 |
| AP | mol H ⁺ -eq. | 0.0300 | 0.0313 | 7.38E-06 | 3.04E-05 | 5.50E-04 | 3.79E-05 | -0.00269 |
| EP-freshwater | kg P-eq. | 2.11E-06 | 2.90E-06 | 2.73E-10 | 1.94E-09 | 5.98E-08 | 9.22E-09 | -4.99E-07 |
| EP-marine | kg N-eq. | 0.00640 | 0.00672 | 3.57E-06 | 1.37E-05 | 1.18E-04 | 9.24E-06 | -1.84E-04 |
| EP-terrestrial | mol N-eq. | 0.0716 | 0.0750 | 3.91E-05 | 1.51E-04 | 0.00129 | 1.01E-04 | 3.85E-04 |
| POCP | kg NMVOC-eq. | 0.0210 | 0.0220 | 9.99E-06 | 2.94E-05 | 3.27E-04 | 2.92E-05 | -0.00191 |
| ADP-minerals & metals ²¹ | kg Sb-eq. | 3.44E-05 | 3.51E-05 | 1.90E-11 | 2.12E-10 | 9.18E-09 | 8.38E-10 | -1.41E-07 |
| ADP-fossil ²¹ | MJ | 84.2 | 87.9 | 0.0206 | 0.156 | 1.18 | 0.170 | -25.4 |
| WDP ²¹ | m ³ world-eq. deprived | 0.751 | 0.799 | 1.15E-05 | 7.46E-05 | 0.0428 | 8.15E-04 | -0.539 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ²² | kg CO ₂ -eq. | 8.22 | 8.55 | 0.00154 | 0.0117 | 0.109 | 0.0117 | -2.70 |
| PM | Disease incidence | 3.80E-07 | 3.94E-07 | 8.35E-11 | 1.99E-10 | 5.36E-09 | 4.05E-10 | -2.96E-08 |
| IRP ²³ | kBq U-235-eq. | 0.128 | 0.131 | 3.91E-08 | 3.97E-06 | 2.07E-05 | 3.03E-04 | 0.0661 |
| ETP-fw ²¹ | CTUe | 14.7 | 15.7 | 0.00518 | 0.0627 | 0.226 | 0.0506 | -0.793 |
| HTP-c ²¹ | CTUh | 1.06E-09 | 1.12E-09 | 8.69E-14 | 1.06E-12 | 1.01E-11 | 5.99E-12 | -1.18E-09 |
| HTP-nc ²¹ | CTUh | 1.48E-07 | 1.54E-07 | 5.43E-12 | 4.20E-11 | 3.37E-10 | 6.03E-10 | -3.85E-08 |
| SQP ²¹ | dimensionless | 3.67 | 5.98 | 4.73E-05 | 4.41E-04 | 0.151 | 0.0132 | 0.346 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 7.50 | 8.47 | 6.73E-05 | 7.64E-04 | 0.255 | 0.0139 | 1.73 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 7.50 | 8.47 | 6.73E-05 | 7.64E-04 | 0.255 | 0.0139 | 1.73 |
| PENRE | MJ | 84.2 | 87.9 | 0.0206 | 0.156 | 1.18 | 0.170 | -25.4 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 84.2 | 87.9 | 0.0206 | 0.156 | 1.18 | 0.170 | -25.4 |
| SM | kg | 0.455 | 0.464 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0209 | 0.0220 | 1.74E-07 | 1.49E-06 | 6.02E-04 | 2.40E-05 | -0.0122 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 2.99E-09 | 7.79E-09 | 2.24E-14 | 2.54E-13 | 3.95E-11 | 2.57E-11 | -1.89E-10 |
| NHWD | kg | 0.235 | 0.244 | 2.95E-07 | 3.79E-06 | 3.69E-04 | 0.249 | 0.504 |
| RWD | kg | 7.05E-04 | 7.24E-04 | 3.02E-10 | 3.05E-08 | 1.61E-07 | 2.05E-06 | 5.42E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.00 | 1.02 | 0 | 0 | 2.24 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 2.24 |
| Steel collected with mixed construction waste | kg | 0.249 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 2.24 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.249 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0226 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.30mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 8.17 | 8.43 | 0.00153 | 0.0116 | 0.108 | 0.0114 | -2.67 |
| ODP | kg CFC11-eq. | 5.85E-12 | 6.52E-12 | 1.45E-16 | 1.39E-15 | 5.73E-13 | 1.86E-14 | 5.56E-14 |
| AP | kg SO ₂ -eq. | 0.0243 | 0.0253 | 5.13E-06 | 2.14E-05 | 4.50E-04 | 3.04E-05 | -0.00248 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00229 | 0.00242 | 1.19E-06 | 4.66E-06 | 4.06E-05 | 3.25E-06 | -6.18E-05 |
| POCP | kg ethene-eq. | 0.00338 | 0.00348 | 5.06E-07 | -5.68E-06 | 2.41E-05 | 2.84E-06 | -0.00120 |
| ADPE | kg Sb-eq. | 3.45E-05 | 3.51E-05 | 1.90E-11 | 2.13E-10 | 9.18E-09 | 8.51E-10 | -1.37E-07 |
| ADPF | MJ | 81.8 | 85.4 | 0.0206 | 0.156 | 1.18 | 0.165 | -26.1 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.18E-10 | 2.30E-10 | 2.36E-15 | 3.24E-14 | 3.92E-12 | 5.24E-13 | 4.95E-11 |
| HTnc - GS | CTUh | 5.76E-11 | 2.46E-10 | 1.13E-15 | 7.30E-15 | 1.25E-13 | 1.22E-14 | 1.38E-12 |
| LU - GS | kg C deficit-eq. | 0.881 | 1.02 | 3.91E-06 | 3.02E-05 | 0.0123 | 0.00115 | 0.144 |
| RDW - GS | m ³ -eq. | 0.00907 | 0.00967 | 1.12E-07 | 9.47E-07 | 4.00E-04 | 1.21E-05 | -0.00666 |
| IR - GS | kBq U235-eq. | 0.128 | 0.131 | 3.91E-08 | 3.97E-06 | 2.07E-05 | 3.03E-04 | 0.0661 |
| PM - GS | kg PM2.5-eq. | 0.00198 | 0.00206 | 3.68E-07 | 1.00E-06 | 2.95E-05 | 2.14E-06 | -1.93E-04 |

21. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

22. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

23. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.35mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 2.88 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 9.42 | 9.73 | 0.00180 | 0.0137 | 0.127 | 0.0140 | -3.27 |
| GWP-fossil | kg CO ₂ -eq. | 9.43 | 9.80 | 0.00180 | 0.0137 | 0.127 | 0.0139 | -3.27 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00198 | -0.0765 | 1.78E-07 | 4.55E-06 | 1.42E-04 | 2.75E-05 | 0.00193 |
| GWP-luluc | kg CO ₂ -eq. | 3.99E-04 | 7.48E-04 | 1.31E-08 | 1.47E-07 | 4.86E-06 | 8.37E-06 | -6.58E-05 |
| ODP | kg CFC-11-eq. | 5.31E-12 | 5.91E-12 | 1.43E-16 | 1.37E-15 | 5.64E-13 | 1.83E-14 | 5.45E-14 |
| AP | mol H ⁺ -eq. | 0.0334 | 0.0348 | 8.55E-06 | 3.52E-05 | 6.37E-04 | 4.39E-05 | -0.00317 |
| EP-freshwater | kg P-eq. | 2.26E-06 | 3.18E-06 | 3.16E-10 | 2.24E-09 | 6.93E-08 | 1.07E-08 | -5.82E-07 |
| EP-marine | kg N-eq. | 0.00714 | 0.00751 | 4.13E-06 | 1.59E-05 | 1.37E-04 | 1.07E-05 | -2.23E-04 |
| EP-terrestrial | mol N-eq. | 0.0801 | 0.0839 | 4.52E-05 | 1.75E-04 | 0.00149 | 1.17E-04 | 3.51E-04 |
| POCP | kg NMVOC-eq. | 0.0236 | 0.0247 | 1.16E-05 | 3.40E-05 | 3.79E-04 | 3.38E-05 | -0.00225 |
| ADP-minerals & metals ²⁴ | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.20E-11 | 2.46E-10 | 1.06E-08 | 9.70E-10 | -1.65E-07 |
| ADP-fossil ²⁴ | MJ | 94.0 | 98.2 | 0.0239 | 0.181 | 1.37 | 0.197 | -29.6 |
| WDP ²⁴ | m ³ world-eq. deprived | 0.796 | 0.850 | 1.34E-05 | 8.63E-05 | 0.0496 | 9.44E-04 | -0.628 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ²⁵ | kg CO ₂ -eq. | 9.22 | 9.60 | 0.00178 | 0.0135 | 0.126 | 0.0135 | -3.15 |
| PM | Disease incidence | 4.25E-07 | 4.41E-07 | 9.67E-11 | 2.31E-10 | 6.21E-09 | 4.69E-10 | -3.51E-08 |
| IRP ²⁶ | kBq U-235-eq. | 0.130 | 0.133 | 4.53E-08 | 4.60E-06 | 2.40E-05 | 3.51E-04 | 0.0770 |
| ETP-fw ²⁴ | CTUe | 16.0 | 17.1 | 0.00600 | 0.0726 | 0.262 | 0.0585 | -0.935 |
| HTP-c ²⁴ | CTUh | 1.14E-09 | 1.20E-09 | 1.01E-13 | 1.23E-12 | 1.17E-11 | 6.94E-12 | -1.37E-09 |
| HTP-nc ²⁴ | CTUh | 1.69E-07 | 1.75E-07 | 6.28E-12 | 4.86E-11 | 3.90E-10 | 6.99E-10 | -4.49E-08 |
| SQP ²⁴ | dimensionless | 3.91 | 6.58 | 5.48E-05 | 5.11E-04 | 0.175 | 0.0153 | 0.402 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 7.75 | 8.86 | 7.80E-05 | 8.84E-04 | 0.295 | 0.0161 | 2.01 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 7.75 | 8.86 | 7.80E-05 | 8.84E-04 | 0.295 | 0.0161 | 2.01 |
| PENRE | MJ | 93.9 | 98.2 | 0.0239 | 0.181 | 1.37 | 0.197 | -29.6 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 94.0 | 98.2 | 0.0239 | 0.181 | 1.37 | 0.197 | -29.6 |
| SM | kg | 0.531 | 0.541 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0217 | 0.0229 | 2.01E-07 | 1.72E-06 | 6.97E-04 | 2.78E-05 | -0.0142 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.16E-09 | 8.71E-09 | 2.59E-14 | 2.94E-13 | 4.58E-11 | 2.98E-11 | -2.22E-10 |
| NHWD | kg | 0.238 | 0.249 | 3.41E-07 | 4.39E-06 | 4.27E-04 | 0.288 | 0.571 |
| RWD | kg | 7.14E-04 | 7.34E-04 | 3.50E-10 | 3.53E-08 | 1.87E-07 | 2.38E-06 | 6.17E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.17 | 1.19 | 0 | 0 | 2.59 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 2.59 |
| Steel collected with mixed construction waste | kg | 0.288 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 2.59 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.288 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0258 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.35mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 9.17 | 9.46 | 0.00177 | 0.0135 | 0.125 | 0.0132 | -3.11 |
| ODP | kg CFC11-eq. | 6.27E-12 | 7.02E-12 | 1.68E-16 | 1.61E-15 | 6.64E-13 | 2.15E-14 | 6.30E-14 |
| AP | kg SO ₂ -eq. | 0.0270 | 0.0282 | 5.94E-06 | 2.48E-05 | 5.21E-04 | 3.52E-05 | -0.00291 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00256 | 0.00270 | 1.38E-06 | 5.39E-06 | 4.70E-05 | 3.76E-06 | -7.50E-05 |
| POCP | kg ethene-eq. | 0.00384 | 0.00396 | 5.86E-07 | -6.58E-06 | 2.79E-05 | 3.29E-06 | -0.00140 |
| ADPE | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.20E-11 | 2.46E-10 | 1.06E-08 | 9.85E-10 | -1.59E-07 |
| ADPF | MJ | 91.5 | 95.6 | 0.0239 | 0.181 | 1.36 | 0.190 | -30.4 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.25E-10 | 2.38E-10 | 2.73E-15 | 3.76E-14 | 4.54E-12 | 6.07E-13 | 5.77E-11 |
| HTnc - GS | CTUh | 6.18E-11 | 2.79E-10 | 1.30E-15 | 8.46E-15 | 1.45E-13 | 1.41E-14 | 1.61E-12 |
| LU - GS | kg C deficit-eq. | 0.992 | 1.15 | 4.52E-06 | 3.50E-05 | 0.0142 | 0.00134 | 0.167 |
| RDW - GS | m ³ -eq. | 0.00956 | 0.0102 | 1.29E-07 | 1.10E-06 | 4.63E-04 | 1.40E-05 | -0.00776 |
| IR - GS | kBq U235-eq. | 0.130 | 0.133 | 4.53E-08 | 4.60E-06 | 2.40E-05 | 3.51E-04 | 0.0770 |
| PM - GS | kg PM2.5-eq. | 0.00222 | 0.00230 | 4.26E-07 | 1.16E-06 | 3.42E-05 | 2.48E-06 | -2.28E-04 |

24. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

25. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

26. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.38mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 3.12 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 10.0 | 10.4 | 0.00195 | 0.0148 | 0.137 | 0.0151 | -3.54 |
| GWP-fossil | kg CO ₂ -eq. | 10.0 | 10.4 | 0.00195 | 0.0148 | 0.137 | 0.0151 | -3.55 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00179 | -0.0824 | 1.93E-07 | 4.92E-06 | 1.53E-04 | 2.97E-05 | 0.00209 |
| GWP-luluc | kg CO ₂ -eq. | 4.07E-04 | 7.85E-04 | 1.41E-08 | 1.59E-07 | 5.26E-06 | 9.05E-06 | -716E-05 |
| ODP | kg CFC-11-eq. | 5.51E-12 | 6.17E-12 | 1.54E-16 | 1.48E-15 | 6.10E-13 | 1.98E-14 | 5.84E-14 |
| AP | mol H ⁺ -eq. | 0.0354 | 0.0369 | 9.25E-06 | 3.81E-05 | 6.89E-04 | 4.75E-05 | -0.00345 |
| EP-freshwater | kg P-eq. | 2.35E-06 | 3.34E-06 | 3.42E-10 | 2.43E-09 | 7.49E-08 | 1.15E-08 | -6.32E-07 |
| EP-marine | kg N-eq. | 0.00759 | 0.00798 | 4.47E-06 | 1.72E-05 | 1.48E-04 | 1.16E-05 | -2.47E-04 |
| EP-terrestrial | mol N-eq. | 0.0852 | 0.0893 | 4.89E-05 | 1.89E-04 | 0.00161 | 1.27E-04 | 3.31E-04 |
| POCP | kg NMVOC-eq. | 0.0251 | 0.0263 | 1.25E-05 | 3.68E-05 | 4.10E-04 | 3.66E-05 | -0.00245 |
| ADP-minerals & metals ²⁷ | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.38E-11 | 2.66E-10 | 1.15E-08 | 1.05E-09 | -1.79E-07 |
| ADP-fossil ²⁷ | MJ | 99.8 | 104 | 0.0258 | 0.196 | 1.48 | 0.213 | -32.1 |
| WDP ²⁷ | m ³ world-eq. deprived | 0.822 | 0.880 | 1.44E-05 | 9.34E-05 | 0.0536 | 0.00102 | -0.681 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ²⁸ | kg CO ₂ -eq. | 9.82 | 10.2 | 0.00192 | 0.0146 | 0.136 | 0.0146 | -3.41 |
| PM | Disease incidence | 4.52E-07 | 4.69E-07 | 1.05E-10 | 2.50E-10 | 6.72E-09 | 5.08E-10 | -3.83E-08 |
| IRP ²⁹ | kBq U-235-eq. | 0.130 | 0.134 | 4.90E-08 | 4.97E-06 | 2.59E-05 | 3.80E-04 | 0.0835 |
| ETP-fw ²⁷ | CTUe | 16.7 | 17.9 | 0.00649 | 0.0785 | 0.283 | 0.0633 | -1.02 |
| HTP-c ²⁷ | CTUh | 1.19E-09 | 1.26E-09 | 1.09E-13 | 1.33E-12 | 1.27E-11 | 7.50E-12 | -1.49E-09 |
| HTP-nc ²⁷ | CTUh | 1.82E-07 | 1.88E-07 | 6.80E-12 | 5.26E-11 | 4.22E-10 | 7.56E-10 | -4.87E-08 |
| SQP ²⁷ | dimensionless | 4.06 | 6.94 | 5.93E-05 | 5.52E-04 | 0.190 | 0.0166 | 0.436 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 7.91 | 9.10 | 8.44E-05 | 9.57E-04 | 0.319 | 0.0174 | 2.18 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 7.91 | 9.10 | 8.44E-05 | 9.57E-04 | 0.319 | 0.0174 | 2.18 |
| PENRE | MJ | 99.8 | 104 | 0.0258 | 0.196 | 1.48 | 0.213 | -32.1 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 99.8 | 104 | 0.0258 | 0.196 | 1.48 | 0.213 | -32.1 |
| SM | kg | 0.577 | 0.587 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0222 | 0.0235 | 2.17E-07 | 1.87E-06 | 7.54E-04 | 3.01E-05 | -0.0154 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.27E-09 | 9.27E-09 | 2.80E-14 | 3.18E-13 | 4.95E-11 | 3.22E-11 | -2.42E-10 |
| NHWD | kg | 0.240 | 0.251 | 3.69E-07 | 4.75E-06 | 4.62E-04 | 0.312 | 0.611 |
| RWD | kg | 7.19E-04 | 7.40E-04 | 3.78E-10 | 3.82E-08 | 2.02E-07 | 2.57E-06 | 6.62E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.26 | 1.29 | 0 | 0 | 2.80 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 2.80 |
| Steel collected with mixed construction waste | kg | 0.312 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 2.80 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.312 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0278 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.38mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 9.76 | 10.1 | 0.00192 | 0.0146 | 0.135 | 0.0143 | -3.37 |
| ODP | kg CFC11-eq. | 6.51E-12 | 7.32E-12 | 1.82E-16 | 1.74E-15 | 7.18E-13 | 2.33E-14 | 6.75E-14 |
| AP | kg SO ₂ -eq. | 0.0287 | 0.0299 | 6.43E-06 | 2.68E-05 | 5.64E-04 | 3.81E-05 | -0.00317 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00273 | 0.00287 | 1.50E-06 | 5.83E-06 | 5.08E-05 | 4.07E-06 | -8.28E-05 |
| POCP | kg ethene-eq. | 0.00412 | 0.00425 | 6.34E-07 | -712E-06 | 3.02E-05 | 3.56E-06 | -0.00152 |
| ADPE | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.38E-11 | 2.66E-10 | 1.15E-08 | 1.07E-09 | -1.73E-07 |
| ADPF | MJ | 97.3 | 102 | 0.0258 | 0.195 | 1.47 | 0.206 | -33.0 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.29E-10 | 2.43E-10 | 2.95E-15 | 4.06E-14 | 4.91E-12 | 6.56E-13 | 6.25E-11 |
| HTnc - GS | CTUh | 6.42E-11 | 2.99E-10 | 1.41E-15 | 9.15E-15 | 1.56E-13 | 1.53E-14 | 1.74E-12 |
| LU - GS | kg C deficit-eq. | 1.06 | 1.23 | 4.89E-06 | 3.79E-05 | 0.0154 | 0.00145 | 0.182 |
| RDW - GS | m ³ -eq. | 0.00985 | 0.0106 | 1.40E-07 | 1.19E-06 | 5.01E-04 | 1.51E-05 | -0.00841 |
| IR - GS | kBq U235-eq. | 0.130 | 0.134 | 4.90E-08 | 4.97E-06 | 2.59E-05 | 3.80E-04 | 0.0835 |
| PM - GS | kg PM2.5-eq. | 0.00236 | 0.00245 | 4.61E-07 | 1.26E-06 | 3.70E-05 | 2.68E-06 | -2.49E-04 |

27. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

28. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

29. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.40mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 3.27 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 10.5 | 10.8 | 0.00204 | 0.0155 | 0.144 | 0.0159 | -3.73 |
| GWP-fossil | kg CO ₂ -eq. | 10.5 | 10.9 | 0.00204 | 0.0155 | 0.144 | 0.0158 | -3.73 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00167 | -0.0863 | 2.02E-07 | 5.17E-06 | 1.61E-04 | 3.12E-05 | 0.00220 |
| GWP-luluc | kg CO ₂ -eq. | 4.13E-04 | 8.10E-04 | 1.48E-08 | 1.67E-07 | 5.53E-06 | 9.51E-06 | -7.55E-05 |
| ODP | kg CFC-11-eq. | 5.65E-12 | 6.34E-12 | 1.62E-16 | 1.56E-15 | 6.41E-13 | 2.08E-14 | 6.09E-14 |
| AP | mol H ⁺ -eq. | 0.0368 | 0.0383 | 9.71E-06 | 4.00E-05 | 7.24E-04 | 4.99E-05 | -0.00364 |
| EP-freshwater | kg P-eq. | 2.40E-06 | 3.45E-06 | 3.59E-10 | 2.55E-09 | 7.87E-08 | 1.21E-08 | -6.65E-07 |
| EP-marine | kg N-eq. | 0.00789 | 0.00830 | 4.69E-06 | 1.81E-05 | 1.55E-04 | 1.22E-05 | -2.62E-04 |
| EP-terrestrial | mol N-eq. | 0.0886 | 0.0928 | 5.14E-05 | 1.99E-04 | 0.00169 | 1.33E-04 | 3.17E-04 |
| POCP | kg NMVOC-eq. | 0.0262 | 0.0274 | 1.31E-05 | 3.86E-05 | 4.30E-04 | 3.85E-05 | -0.00259 |
| ADP-minerals & metals ³⁰ | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.49E-11 | 2.79E-10 | 1.21E-08 | 1.10E-09 | -1.88E-07 |
| ADP-fossil ³⁰ | MJ | 104 | 108 | 0.0271 | 0.206 | 1.56 | 0.224 | -33.8 |
| WDP ³⁰ | m ³ world-eq. deprived | 0.840 | 0.901 | 1.52E-05 | 9.81E-05 | 0.0563 | 0.00107 | -0.717 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ³¹ | kg CO ₂ -eq. | 10.2 | 10.6 | 0.00202 | 0.0154 | 0.143 | 0.0153 | -3.59 |
| PM | Disease incidence | 4.70E-07 | 4.87E-07 | 1.10E-10 | 2.62E-10 | 7.05E-09 | 5.33E-10 | -4.05E-08 |
| IRP ³² | kBq U-235-eq. | 0.131 | 0.134 | 5.15E-08 | 5.22E-06 | 2.72E-05 | 3.99E-04 | 0.0879 |
| ETP-fw ³⁰ | CTUe | 17.2 | 18.5 | 0.00681 | 0.0825 | 0.297 | 0.0665 | -1.08 |
| HTP-c ³⁰ | CTUh | 1.22E-09 | 1.29E-09 | 1.14E-13 | 1.39E-12 | 1.33E-11 | 7.88E-12 | -1.57E-09 |
| HTP-nc ³⁰ | CTUh | 1.90E-07 | 1.97E-07 | 7.14E-12 | 5.53E-11 | 4.43E-10 | 7.94E-10 | -5.13E-08 |
| SQP ³⁰ | dimensionless | 4.16 | 7.18 | 6.23E-05 | 5.80E-04 | 0.199 | 0.0174 | 0.458 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 8.01 | 9.25 | 8.86E-05 | 0.00101 | 0.335 | 0.0183 | 2.29 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 8.01 | 9.25 | 8.86E-05 | 0.00101 | 0.335 | 0.0183 | 2.29 |
| PENRE | MJ | 104 | 108 | 0.0271 | 0.206 | 1.56 | 0.224 | -33.8 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 104 | 109 | 0.0271 | 0.206 | 1.56 | 0.224 | -33.8 |
| SM | kg | 0.607 | 0.618 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0225 | 0.0239 | 2.28E-07 | 1.96E-06 | 7.91E-04 | 3.16E-05 | -0.0162 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.34E-09 | 9.64E-09 | 2.94E-14 | 3.34E-13 | 5.20E-11 | 3.39E-11 | -2.55E-10 |
| NHWD | kg | 0.242 | 0.253 | 3.87E-07 | 4.99E-06 | 4.86E-04 | 0.328 | 0.638 |
| RWD | kg | 7.23E-04 | 7.44E-04 | 3.98E-10 | 4.02E-08 | 2.12E-07 | 2.70E-06 | 6.92E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.33 | 1.36 | 0 | 0 | 2.95 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 2.95 |
| Steel collected with mixed construction waste | kg | 0.327 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 2.95 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.327 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0291 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.40mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 10.2 | 10.5 | 0.00201 | 0.0153 | 0.142 | 0.0150 | -3.55 |
| ODP | kg CFC11-eq. | 6.68E-12 | 7.53E-12 | 1.91E-16 | 1.83E-15 | 7.54E-13 | 2.45E-14 | 7.04E-14 |
| AP | kg SO ₂ -eq. | 0.0297 | 0.0310 | 6.75E-06 | 2.82E-05 | 5.92E-04 | 4.00E-05 | -0.00335 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00283 | 0.00299 | 1.57E-06 | 6.12E-06 | 5.34E-05 | 4.27E-06 | -8.81E-05 |
| POCP | kg ethene-eq. | 0.00431 | 0.00444 | 6.66E-07 | -7.48E-06 | 3.17E-05 | 3.74E-06 | -0.00160 |
| ADPE | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.50E-11 | 2.80E-10 | 1.21E-08 | 1.12E-09 | -1.82E-07 |
| ADPF | MJ | 101 | 106 | 0.0271 | 0.205 | 1.55 | 0.216 | -34.7 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.32E-10 | 2.46E-10 | 3.10E-15 | 4.27E-14 | 5.16E-12 | 6.89E-13 | 6.58E-11 |
| HTnc - GS | CTUh | 6.59E-11 | 3.13E-10 | 1.48E-15 | 9.61E-15 | 1.64E-13 | 1.60E-14 | 1.83E-12 |
| LU - GS | kg C deficit-eq. | 1.10 | 1.28 | 5.14E-06 | 3.98E-05 | 0.0162 | 0.00152 | 0.191 |
| RDW - GS | m ³ -eq. | 0.0100 | 0.0108 | 1.47E-07 | 1.25E-06 | 5.26E-04 | 1.59E-05 | -0.00885 |
| IR - GS | kBq U235-eq. | 0.131 | 0.134 | 5.15E-08 | 5.22E-06 | 2.72E-05 | 3.99E-04 | 0.0878 |
| PM - GS | kg PM2.5-eq. | 0.00245 | 0.00254 | 4.85E-07 | 1.32E-06 | 3.88E-05 | 2.82E-06 | -2.62E-04 |

30. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

31. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

32. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.42mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 3.43 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 10.9 | 11.2 | 0.00214 | 0.0163 | 0.151 | 0.0166 | -3.91 |
| GWP-fossil | kg CO ₂ -eq. | 10.9 | 11.3 | 0.00214 | 0.0163 | 0.151 | 0.0166 | -3.92 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00154 | -0.0903 | 2.12E-07 | 5.42E-06 | 1.69E-04 | 3.27E-05 | 0.00230 |
| GWP-luluc | kg CO ₂ -eq. | 4.19E-04 | 8.35E-04 | 1.55E-08 | 1.75E-07 | 5.79E-06 | 9.96E-06 | -7.93E-05 |
| ODP | kg CFC-11-eq. | 5.79E-12 | 6.51E-12 | 1.70E-16 | 1.63E-15 | 6.71E-13 | 2.18E-14 | 6.35E-14 |
| AP | mol H ⁺ -eq. | 0.0381 | 0.0397 | 1.02E-05 | 4.19E-05 | 7.59E-04 | 5.23E-05 | -0.00384 |
| EP-freshwater | kg P-eq. | 2.46E-06 | 3.55E-06 | 3.76E-10 | 2.67E-09 | 8.25E-08 | 1.27E-08 | -6.98E-07 |
| EP-marine | kg N-eq. | 0.00819 | 0.00862 | 4.92E-06 | 1.90E-05 | 1.63E-04 | 1.27E-05 | -2.78E-04 |
| EP-terrestrial | mol N-eq. | 0.0919 | 0.0964 | 5.39E-05 | 2.08E-04 | 0.00177 | 1.40E-04 | 3.03E-04 |
| POCP | kg NMVOC-eq. | 0.0272 | 0.0285 | 1.38E-05 | 4.05E-05 | 4.51E-04 | 4.03E-05 | -0.00272 |
| ADP-minerals & metals ³³ | kg Sb-eq. | 3.45E-05 | 3.52E-05 | 2.61E-11 | 2.93E-10 | 1.27E-08 | 1.15E-09 | -1.98E-07 |
| ADP-fossil ³³ | MJ | 108 | 113 | 0.0284 | 0.216 | 1.63 | 0.235 | -35.5 |
| WDP ³³ | m ³ world-eq. deprived | 0.858 | 0.921 | 1.59E-05 | 1.03E-04 | 0.0590 | 0.00112 | -0.752 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ³⁴ | kg CO ₂ -eq. | 10.6 | 11.1 | 0.00212 | 0.0161 | 0.150 | 0.0161 | -3.77 |
| PM | Disease incidence | 4.88E-07 | 5.06E-07 | 1.15E-10 | 2.75E-10 | 7.39E-09 | 5.59E-10 | -4.26E-08 |
| IRP ³⁵ | kBq U-235-eq. | 0.132 | 0.135 | 5.39E-08 | 5.47E-06 | 2.85E-05 | 4.18E-04 | 0.0922 |
| ETP-fw ³³ | CTUe | 17.7 | 19.0 | 0.00714 | 0.0864 | 0.311 | 0.0697 | -1.13 |
| HTP-c ³³ | CTUh | 1.25E-09 | 1.32E-09 | 1.20E-13 | 1.46E-12 | 1.40E-11 | 8.26E-12 | -1.64E-09 |
| HTP-nc ³³ | CTUh | 1.98E-07 | 2.05E-07 | 7.48E-12 | 5.79E-11 | 4.65E-10 | 8.32E-10 | -5.38E-08 |
| SQP ³³ | dimensionless | 4.26 | 7.42 | 6.53E-05 | 6.08E-04 | 0.209 | 0.0183 | 0.480 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 8.12 | 9.41 | 9.29E-05 | 0.00105 | 0.351 | 0.0192 | 2.40 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 8.12 | 9.41 | 9.29E-05 | 0.00105 | 0.351 | 0.0192 | 2.40 |
| PENRE | MJ | 108 | 113 | 0.0284 | 0.216 | 1.63 | 0.235 | -35.5 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 108 | 113 | 0.0284 | 0.216 | 1.63 | 0.235 | -35.5 |
| SM | kg | 0.637 | 0.649 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0229 | 0.0243 | 2.39E-07 | 2.05E-06 | 8.29E-04 | 3.31E-05 | -0.0170 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.41E-09 | 1.00E-08 | 3.08E-14 | 3.50E-13 | 5.45E-11 | 3.55E-11 | -2.68E-10 |
| NHWD | kg | 0.243 | 0.255 | 4.06E-07 | 5.23E-06 | 5.09E-04 | 0.343 | 0.665 |
| RWD | kg | 7.27E-04 | 7.48E-04 | 4.17E-10 | 4.21E-08 | 2.22E-07 | 2.83E-06 | 7.22E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.40 | 1.42 | 0 | 0 | 3.09 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 3.09 |
| Steel collected with mixed construction waste | kg | 0.343 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 3.09 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.343 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0304 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.42mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 10.6 | 10.9 | 0.00211 | 0.0160 | 0.149 | 0.0157 | -3.72 |
| ODP | kg CFC11-eq. | 6.84E-12 | 7.73E-12 | 2.00E-16 | 1.92E-15 | 7.90E-13 | 2.57E-14 | 7.34E-14 |
| AP | kg SO ₂ -eq. | 0.0308 | 0.0321 | 7.07E-06 | 2.95E-05 | 6.20E-04 | 4.20E-05 | -0.00352 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00294 | 0.00310 | 1.65E-06 | 6.42E-06 | 5.59E-05 | 4.48E-06 | -9.34E-05 |
| POCP | kg ethene-eq. | 0.00450 | 0.00464 | 6.98E-07 | -7.84E-06 | 3.32E-05 | 3.92E-06 | -0.00168 |
| ADPE | kg Sb-eq. | 3.46E-05 | 3.52E-05 | 2.62E-11 | 2.93E-10 | 1.27E-08 | 1.17E-09 | -1.91E-07 |
| ADPF | MJ | 105 | 110 | 0.0284 | 0.215 | 1.62 | 0.227 | -36.4 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.35E-10 | 2.50E-10 | 3.25E-15 | 4.47E-14 | 5.40E-12 | 7.22E-13 | 6.90E-11 |
| HTnc - GS | CTUh | 6.75E-11 | 3.26E-10 | 1.55E-15 | 1.01E-14 | 1.72E-13 | 1.68E-14 | 1.92E-12 |
| LU - GS | kg C deficit-eq. | 1.15 | 1.33 | 5.39E-06 | 4.17E-05 | 0.0170 | 0.00159 | 0.200 |
| RDW - GS | m ³ -eq. | 0.0102 | 0.0110 | 1.54E-07 | 1.31E-06 | 5.51E-04 | 1.66E-05 | -0.00929 |
| IR - GS | kBq U235-eq. | 0.132 | 0.135 | 5.39E-08 | 5.47E-06 | 2.85E-05 | 4.18E-04 | 0.0922 |
| PM - GS | kg PM2.5-eq. | 0.00254 | 0.00264 | 5.08E-07 | 1.38E-06 | 4.07E-05 | 2.96E-06 | -2.76E-04 |

33. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

34. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

35. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.48mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 3.90 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 12.1 | 12.5 | 0.00244 | 0.0185 | 0.172 | 0.0189 | -4.47 |
| GWP-fossil | kg CO ₂ -eq. | 12.1 | 12.6 | 0.00244 | 0.0185 | 0.172 | 0.0188 | -4.47 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00117 | -0.102 | 2.41E-07 | 6.16E-06 | 1.92E-04 | 3.72E-05 | 0.00262 |
| GWP-luluc | kg CO ₂ -eq. | 4.37E-04 | 9.09E-04 | 1.77E-08 | 1.99E-07 | 6.59E-06 | 1.13E-05 | -9.10E-05 |
| ODP | kg CFC-11-eq. | 6.21E-12 | 7.01E-12 | 1.93E-16 | 1.86E-15 | 7.63E-13 | 2.48E-14 | 7.13E-14 |
| AP | mol H ⁺ -eq. | 0.0421 | 0.0440 | 1.16E-05 | 4.77E-05 | 8.63E-04 | 5.95E-05 | -0.00441 |
| EP-freshwater | kg P-eq. | 2.64E-06 | 3.88E-06 | 4.28E-10 | 3.04E-09 | 9.38E-08 | 1.45E-08 | -7.97E-07 |
| EP-marine | kg N-eq. | 0.00908 | 0.00956 | 5.59E-06 | 2.16E-05 | 1.85E-04 | 1.45E-05 | -3.25E-04 |
| EP-terrestrial | mol N-eq. | 0.102 | 0.107 | 6.13E-05 | 2.37E-04 | 0.00202 | 1.59E-04 | 2.63E-04 |
| POCP | kg NMVOC-eq. | 0.0303 | 0.0317 | 1.57E-05 | 4.60E-05 | 5.13E-04 | 4.58E-05 | -0.00313 |
| ADP-minerals & metals ³⁶ | kg Sb-eq. | 3.46E-05 | 3.53E-05 | 2.97E-11 | 3.33E-10 | 1.44E-08 | 1.31E-09 | -2.26E-07 |
| ADP-fossil ³⁶ | MJ | 119 | 125 | 0.0323 | 0.245 | 1.85 | 0.267 | -40.5 |
| WDP ³⁶ | m ³ world-eq. deprived | 0.912 | 0.982 | 1.81E-05 | 1.17E-04 | 0.0671 | 0.00128 | -0.859 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ³⁷ | kg CO ₂ -eq. | 11.8 | 12.3 | 0.00241 | 0.0183 | 0.170 | 0.0183 | -4.30 |
| PM | Disease incidence | 5.42E-07 | 5.62E-07 | 1.31E-10 | 3.13E-10 | 8.41E-09 | 6.36E-10 | -4.92E-08 |
| IRP ³⁸ | kBq U-235-eq. | 0.133 | 0.137 | 6.14E-08 | 6.22E-06 | 3.24E-05 | 4.75E-04 | 0.105 |
| ETP-fw ³⁶ | CTUe | 19.2 | 20.6 | 0.00812 | 0.0983 | 0.354 | 0.0793 | -1.30 |
| HTP-c ³⁶ | CTUh | 1.34E-09 | 1.43E-09 | 1.36E-13 | 1.66E-12 | 1.59E-11 | 9.39E-12 | -1.88E-09 |
| HTP-nc ³⁶ | CTUh | 2.23E-07 | 2.31E-07 | 8.51E-12 | 6.59E-11 | 5.29E-10 | 9.46E-10 | -6.15E-08 |
| SQP ³⁶ | dimensionless | 4.55 | 8.15 | 7.42E-05 | 6.91E-04 | 0.237 | 0.0208 | 0.547 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 8.43 | 9.88 | 1.06E-04 | 0.00120 | 0.399 | 0.0218 | 2.74 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 8.43 | 9.88 | 1.06E-04 | 0.00120 | 0.399 | 0.0218 | 2.74 |
| PENRE | MJ | 119 | 125 | 0.0323 | 0.245 | 1.85 | 0.267 | -40.5 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 119 | 125 | 0.0323 | 0.245 | 1.85 | 0.267 | -40.5 |
| SM | kg | 0.728 | 0.742 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0238 | 0.0254 | 2.72E-07 | 2.34E-06 | 9.43E-04 | 3.76E-05 | -0.0194 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.61E-09 | 1.11E-08 | 3.51E-14 | 3.98E-13 | 6.20E-11 | 4.04E-11 | -3.08E-10 |
| NHWD | kg | 0.248 | 0.260 | 4.62E-07 | 5.95E-06 | 5.79E-04 | 0.391 | 0.745 |
| RWD | kg | 7.37E-04 | 7.61E-04 | 4.74E-10 | 4.79E-08 | 2.53E-07 | 3.22E-06 | 8.12E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.59 | 1.62 | 0 | 0 | 3.51 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 3.51 |
| Steel collected with mixed construction waste | kg | 0.390 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 3.51 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.390 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0343 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.48mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 11.8 | 12.1 | 0.00240 | 0.0182 | 0.169 | 0.0179 | -4.25 |
| ODP | kg CFC11-eq. | 7.33E-12 | 8.33E-12 | 2.28E-16 | 2.18E-15 | 8.99E-13 | 2.92E-14 | 8.23E-14 |
| AP | kg SO ₂ -eq. | 0.0341 | 0.0356 | 8.04E-06 | 3.36E-05 | 7.06E-04 | 4.77E-05 | -0.00404 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00327 | 0.00345 | 1.87E-06 | 7.30E-06 | 6.36E-05 | 5.09E-06 | -1.09E-04 |
| POCP | kg ethene-eq. | 0.00506 | 0.00521 | 7.94E-07 | -8.91E-06 | 3.78E-05 | 4.45E-06 | -0.00192 |
| ADPE | kg Sb-eq. | 3.46E-05 | 3.53E-05 | 2.97E-11 | 3.33E-10 | 1.44E-08 | 1.33E-09 | -2.18E-07 |
| ADPF | MJ | 117 | 122 | 0.0323 | 0.245 | 1.85 | 0.258 | -41.6 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.43E-10 | 2.59E-10 | 3.69E-15 | 5.09E-14 | 6.15E-12 | 8.21E-13 | 7.87E-11 |
| HTnc - GS | CTUh | 7.25E-11 | 3.67E-10 | 1.77E-15 | 1.15E-14 | 1.96E-13 | 1.91E-14 | 2.19E-12 |
| LU - GS | kg C deficit-eq. | 1.28 | 1.49 | 6.13E-06 | 4.74E-05 | 0.0193 | 0.00181 | 0.229 |
| RDW - GS | m ³ -eq. | 0.0108 | 0.0117 | 1.75E-07 | 1.48E-06 | 6.27E-04 | 1.89E-05 | -0.0106 |
| IR - GS | kBq U235-eq. | 0.133 | 0.137 | 6.13E-08 | 6.22E-06 | 3.24E-05 | 4.75E-04 | 0.105 |
| PM - GS | kg PM2.5-eq. | 0.00282 | 0.00293 | 5.78E-07 | 1.57E-06 | 4.63E-05 | 3.36E-06 | -3.18E-04 |

36. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

37. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

38. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.50mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 4.06 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 12.5 | 12.9 | 0.00253 | 0.0192 | 0.179 | 0.0197 | -4.65 |
| GWP-fossil | kg CO ₂ -eq. | 12.5 | 13.0 | 0.00253 | 0.0192 | 0.179 | 0.0196 | -4.66 |
| GWP-biogenic | kg CO ₂ -eq. | -0.00104 | -0.106 | 2.51E-07 | 6.41E-06 | 1.99E-04 | 3.87E-05 | 0.00272 |
| GWP-luluc | kg CO ₂ -eq. | 4.43E-04 | 9.34E-04 | 1.84E-08 | 2.07E-07 | 6.85E-06 | 1.18E-05 | -9.49E-05 |
| ODP | kg CFC-11-eq. | 6.35E-12 | 7.18E-12 | 2.01E-16 | 1.93E-15 | 7.94E-13 | 2.58E-14 | 7.38E-14 |
| AP | mol H ⁺ -eq. | 0.0435 | 0.0454 | 1.20E-05 | 4.96E-05 | 8.98E-04 | 6.18E-05 | -0.00460 |
| EP-freshwater | kg P-eq. | 2.70E-06 | 3.99E-06 | 4.45E-10 | 3.16E-09 | 9.76E-08 | 1.50E-08 | -8.31E-07 |
| EP-marine | kg N-eq. | 0.00938 | 0.00988 | 5.82E-06 | 2.24E-05 | 1.92E-04 | 1.51E-05 | -3.41E-04 |
| EP-terrestrial | mol N-eq. | 0.105 | 0.111 | 6.37E-05 | 2.47E-04 | 0.00210 | 1.65E-04 | 2.49E-04 |
| POCP | kg NMVOC-eq. | 0.0313 | 0.0328 | 1.63E-05 | 4.79E-05 | 5.34E-04 | 4.77E-05 | -0.00326 |
| ADP-minerals & metals ³⁹ | kg Sb-eq. | 3.46E-05 | 3.53E-05 | 3.09E-11 | 3.46E-10 | 1.50E-08 | 1.37E-09 | -2.35E-07 |
| ADP-fossil ³⁹ | MJ | 123 | 129 | 0.0336 | 0.255 | 1.93 | 0.278 | -42.2 |
| WDP ³⁹ | m ³ world-eq. deprived | 0.930 | 1.00 | 1.88E-05 | 1.22E-04 | 0.0698 | 0.00133 | -0.894 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁴⁰ | kg CO ₂ -eq. | 12.2 | 12.7 | 0.00251 | 0.0190 | 0.177 | 0.0190 | -4.48 |
| PM | Disease incidence | 5.60E-07 | 5.81E-07 | 1.36E-10 | 3.25E-10 | 8.75E-09 | 6.61E-10 | -5.13E-08 |
| IRP ⁴⁰ | kBq U-235-eq. | 0.134 | 0.138 | 6.38E-08 | 6.48E-06 | 3.37E-05 | 4.94E-04 | 0.110 |
| ETP-fw ³⁹ | CTUe | 19.7 | 21.2 | 0.00845 | 0.102 | 0.368 | 0.0825 | -1.36 |
| HTP-c ³⁹ | CTUh | 1.37E-09 | 1.46E-09 | 1.42E-13 | 1.73E-12 | 1.65E-11 | 9.77E-12 | -1.95E-09 |
| HTP-nc ³⁹ | CTUh | 2.32E-07 | 2.40E-07 | 8.85E-12 | 6.85E-11 | 5.50E-10 | 9.84E-10 | -6.40E-08 |
| SQP ³⁹ | dimensionless | 4.65 | 8.39 | 7.72E-05 | 7.19E-04 | 0.247 | 0.0216 | 0.570 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|----------|----------|---------|
| PERE | MJ | 8.53 | 10.0 | 1.10E-04 | 0.00125 | 0.415 | 0.0227 | 2.86 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 8.53 | 10.0 | 1.10E-04 | 0.00125 | 0.415 | 0.0227 | 2.86 |
| PENRE | MJ | 123 | 129 | 0.0336 | 0.255 | 1.93 | 0.278 | -42.2 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 123 | 129 | 0.0336 | 0.255 | 1.93 | 0.278 | -42.2 |
| SM | kg | 0.759 | 0.773 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0242 | 0.0258 | 2.83E-07 | 2.43E-06 | 9.81E-04 | 3.92E-05 | -0.0202 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.68E-09 | 1.15E-08 | 3.65E-14 | 4.14E-13 | 6.45E-11 | 4.20E-11 | -3.21E-10 |
| NHWD | kg | 0.249 | 0.262 | 4.80E-07 | 6.19E-06 | 6.02E-04 | 0.406 | 0.772 |
| RWD | kg | 7.41E-04 | 7.65E-04 | 4.93E-10 | 4.98E-08 | 2.63E-07 | 3.35E-06 | 8.42E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.66 | 1.69 | 0 | 0 | 3.65 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 3.65 |
| Steel collected with mixed construction waste | kg | 0.406 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 3.65 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.406 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0356 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.50mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 12.2 | 12.5 | 0.00250 | 0.0190 | 0.176 | 0.0186 | -4.43 |
| ODP | kg CFC11-eq. | 7.50E-12 | 8.54E-12 | 2.37E-16 | 2.27E-15 | 9.35E-13 | 3.03E-14 | 8.53E-14 |
| AP | kg SO ₂ -eq. | 0.0352 | 0.0367 | 8.37E-06 | 3.49E-05 | 7.34E-04 | 4.96E-05 | -0.00422 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00337 | 0.00356 | 1.95E-06 | 7.59E-06 | 6.62E-05 | 5.30E-06 | -1.14E-04 |
| POCP | kg ethene-eq. | 0.00524 | 0.00541 | 8.26E-07 | -9.27E-06 | 3.93E-05 | 4.63E-06 | -0.00200 |
| ADPE | kg Sb-eq. | 3.46E-05 | 3.53E-05 | 3.09E-11 | 3.47E-10 | 1.50E-08 | 1.39E-09 | -2.27E-07 |
| ADPF | MJ | 121 | 126 | 0.0336 | 0.254 | 1.92 | 0.268 | -43.3 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.46E-10 | 2.63E-10 | 3.84E-15 | 5.29E-14 | 6.39E-12 | 8.55E-13 | 8.20E-11 |
| HTnc - GS | CTUh | 7.41E-11 | 3.80E-10 | 1.84E-15 | 1.19E-14 | 2.04E-13 | 1.99E-14 | 2.28E-12 |
| LU - GS | kg C deficit-eq. | 1.32 | 1.55 | 6.37E-06 | 4.93E-05 | 0.0201 | 0.00188 | 0.238 |
| RDW - GS | m ³ -eq. | 0.0110 | 0.0119 | 1.82E-07 | 1.54E-06 | 6.52E-04 | 1.97E-05 | -0.0110 |
| IR - GS | kBq U235-eq. | 0.134 | 0.137 | 6.38E-08 | 6.47E-06 | 3.37E-05 | 4.94E-04 | 0.110 |
| PM - GS | kg PM2.5-eq. | 0.00291 | 0.00303 | 6.01E-07 | 1.64E-06 | 4.81E-05 | 3.50E-06 | -3.31E-04 |

39. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

40. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

41. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.55mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 4.45 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|-----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 13.5 | 14.0 | 0.00278 | 0.0211 | 0.196 | 0.0216 | -5.12 |
| GWP-fossil | kg CO ₂ -eq. | 13.5 | 14.1 | 0.00278 | 0.0211 | 0.196 | 0.0215 | -5.12 |
| GWP-biogenic | kg CO ₂ -eq. | -7.28E-04 | -0.116 | 2.75E-07 | 7.03E-06 | 2.19E-04 | 4.24E-05 | 0.00299 |
| GWP-luluc | kg CO ₂ -eq. | 4.58E-04 | 9.96E-04 | 2.02E-08 | 2.27E-07 | 7.51E-06 | 1.29E-05 | -1.05E-04 |
| ODP | kg CFC-11-eq. | 6.70E-12 | 7.61E-12 | 2.21E-16 | 2.12E-15 | 8.71E-13 | 2.83E-14 | 8.03E-14 |
| AP | mol H ⁺ -eq. | 0.0469 | 0.0490 | 1.32E-05 | 5.44E-05 | 9.85E-04 | 6.78E-05 | -0.00508 |
| EP-freshwater | kg P-eq. | 2.85E-06 | 4.26E-06 | 4.88E-10 | 3.47E-09 | 1.07E-07 | 1.65E-08 | -9.14E-07 |
| EP-marine | kg N-eq. | 0.0101 | 0.0107 | 6.38E-06 | 2.46E-05 | 2.11E-04 | 1.65E-05 | -3.80E-04 |
| EP-terrestrial | mol N-eq. | 0.114 | 0.120 | 6.99E-05 | 2.71E-04 | 0.00230 | 1.81E-04 | 2.15E-04 |
| POCP | kg NMVOC-eq. | 0.0339 | 0.0355 | 1.79E-05 | 5.25E-05 | 5.85E-04 | 5.23E-05 | -0.00360 |
| ADP-minerals & metals ⁴² | kg Sb-eq. | 3.47E-05 | 3.54E-05 | 3.39E-11 | 3.80E-10 | 1.64E-08 | 1.50E-09 | -2.58E-07 |
| ADP-fossil ⁴² | MJ | 133 | 139 | 0.0369 | 0.280 | 2.12 | 0.305 | -46.4 |
| WDP ⁴² | m ³ world-eq. deprived | 0.974 | 1.05 | 2.06E-05 | 1.33E-04 | 0.0766 | 0.00146 | -0.983 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁴³ | kg CO ₂ -eq. | 13.2 | 13.8 | 0.00275 | 0.0209 | 0.194 | 0.0209 | -4.93 |
| PM | Disease incidence | 6.04E-07 | 6.28E-07 | 1.49E-10 | 3.57E-10 | 9.59E-09 | 7.25E-10 | -5.68E-08 |
| IRP ⁴⁴ | kBq U-235-eq. | 0.136 | 0.139 | 7.00E-08 | 7.10E-06 | 3.70E-05 | 5.42E-04 | 0.120 |
| ETP-fw ⁴² | CTUe | 20.9 | 22.6 | 0.00927 | 0.112 | 0.404 | 0.0904 | -1.50 |
| HTP-c ⁴² | CTUh | 1.45E-09 | 1.55E-09 | 1.56E-13 | 1.89E-12 | 1.81E-11 | 1.07E-11 | -2.15E-09 |
| HTP-nc ⁴² | CTUh | 2.52E-07 | 2.61E-07 | 9.71E-12 | 7.51E-11 | 6.03E-10 | 1.08E-09 | -7.04E-08 |
| SQP ⁴² | dimensionless | 4.89 | 8.99 | 8.47E-05 | 7.89E-04 | 0.271 | 0.0237 | 0.626 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 8.79 | 10.4 | 1.20E-04 | 0.00137 | 0.455 | 0.0249 | 3.14 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 8.79 | 10.4 | 1.20E-04 | 0.00137 | 0.455 | 0.0249 | 3.14 |
| PENRE | MJ | 133 | 139 | 0.0369 | 0.280 | 2.12 | 0.305 | -46.4 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 133 | 139 | 0.0369 | 0.280 | 2.12 | 0.305 | -46.4 |
| SM | kg | 0.834 | 0.850 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0250 | 0.0267 | 3.10E-07 | 2.66E-06 | 0.00108 | 4.30E-05 | -0.0223 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 3.86E-09 | 1.24E-08 | 4.00E-14 | 4.54E-13 | 7.07E-11 | 4.60E-11 | -3.54E-10 |
| NHWD | kg | 0.253 | 0.267 | 5.27E-07 | 6.78E-06 | 6.61E-04 | 0.446 | 0.839 |
| RWD | kg | 7.50E-04 | 7.75E-04 | 5.41E-10 | 5.46E-08 | 2.89E-07 | 3.67E-06 | 9.16E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.82 | 1.86 | 0 | 0 | 4.00 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 4.00 |
| Steel collected with mixed construction waste | kg | 0.445 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 4.00 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.445 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0389 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.55mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 13.1 | 13.6 | 0.00274 | 0.0208 | 0.193 | 0.0204 | -4.87 |
| ODP | kg CFC11-eq. | 7.91E-12 | 9.04E-12 | 2.60E-16 | 2.49E-15 | 1.03E-12 | 3.33E-14 | 9.27E-14 |
| AP | kg SO ₂ -eq. | 0.0379 | 0.0395 | 9.18E-06 | 3.83E-05 | 8.05E-04 | 5.44E-05 | -0.00465 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00364 | 0.00385 | 2.14E-06 | 8.33E-06 | 7.26E-05 | 5.81E-06 | -1.28E-04 |
| POCP | kg ethene-eq. | 0.00571 | 0.00589 | 9.05E-07 | -1.02E-05 | 4.31E-05 | 5.08E-06 | -0.00220 |
| ADPE | kg Sb-eq. | 3.47E-05 | 3.54E-05 | 3.39E-11 | 3.80E-10 | 1.64E-08 | 1.52E-09 | -2.50E-07 |
| ADPF | MJ | 130 | 136 | 0.0369 | 0.279 | 2.11 | 0.294 | -47.6 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.52E-10 | 2.71E-10 | 4.21E-15 | 5.81E-14 | 7.01E-12 | 9.37E-13 | 9.01E-11 |
| HTnc - GS | CTUh | 7.82E-11 | 4.14E-10 | 2.01E-15 | 1.31E-14 | 2.23E-13 | 2.18E-14 | 2.51E-12 |
| LU - GS | kg C deficit-eq. | 1.43 | 1.68 | 6.99E-06 | 5.41E-05 | 0.0220 | 0.00207 | 0.262 |
| RDW - GS | m ³ -eq. | 0.0115 | 0.0125 | 2.00E-07 | 1.69E-06 | 7.15E-04 | 2.16E-05 | -0.0121 |
| IR - GS | kBq U235-eq. | 0.136 | 0.139 | 7.00E-08 | 7.10E-06 | 3.70E-05 | 5.42E-04 | 0.120 |
| PM - GS | kg PM2.5-eq. | 0.00314 | 0.00327 | 6.59E-07 | 1.79E-06 | 5.28E-05 | 3.83E-06 | -3.66E-04 |

42. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

43. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

44. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.60mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 4.84 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|-----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 14.6 | 15.0 | 0.00302 | 0.0230 | 0.213 | 0.0235 | -5.58 |
| GWP-fossil | kg CO ₂ -eq. | 14.6 | 15.2 | 0.00302 | 0.0230 | 0.213 | 0.0234 | -5.58 |
| GWP-biogenic | kg CO ₂ -eq. | -4.15E-04 | -0.126 | 2.99E-07 | 7.65E-06 | 2.38E-04 | 4.62E-05 | 0.00325 |
| GWP-luluc | kg CO ₂ -eq. | 4.73E-04 | 0.00106 | 2.20E-08 | 2.47E-07 | 8.18E-06 | 1.41E-05 | -1.14E-04 |
| ODP | kg CFC-11-eq. | 7.05E-12 | 8.03E-12 | 2.40E-16 | 2.30E-15 | 9.48E-13 | 3.08E-14 | 8.68E-14 |
| AP | mol H ⁺ -eq. | 0.0502 | 0.0525 | 1.44E-05 | 5.92E-05 | 0.00107 | 7.38E-05 | -0.00555 |
| EP-freshwater | kg P-eq. | 3.00E-06 | 4.53E-06 | 5.31E-10 | 3.77E-09 | 1.16E-07 | 1.79E-08 | -9.96E-07 |
| EP-marine | kg N-eq. | 0.0109 | 0.0115 | 6.94E-06 | 2.68E-05 | 2.30E-04 | 1.80E-05 | -4.19E-04 |
| EP-terrestrial | mol N-eq. | 0.122 | 0.129 | 7.60E-05 | 2.94E-04 | 0.00251 | 1.97E-04 | 1.81E-04 |
| POCP | kg NMVOC-eq. | 0.0364 | 0.0382 | 1.95E-05 | 5.72E-05 | 6.37E-04 | 5.69E-05 | -0.00394 |
| ADP-minerals & metals ⁴⁵ | kg Sb-eq. | 3.47E-05 | 3.54E-05 | 3.69E-11 | 4.13E-10 | 1.79E-08 | 1.63E-09 | -2.82E-07 |
| ADP-fossil ⁴⁵ | MJ | 143 | 150 | 0.0401 | 0.304 | 2.30 | 0.332 | -50.6 |
| WDP ⁴⁵ | m ³ world-eq. deprived | 1.02 | 1.10 | 2.24E-05 | 1.45E-04 | 0.0833 | 0.00159 | -1.07 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁴⁶ | kg CO ₂ -eq. | 14.2 | 14.8 | 0.00299 | 0.0227 | 0.211 | 0.0227 | -5.37 |
| PM | Disease incidence | 6.49E-07 | 6.75E-07 | 1.63E-10 | 3.88E-10 | 1.04E-08 | 7.89E-10 | -6.22E-08 |
| IRP ⁴⁷ | kBq U-235-eq. | 0.137 | 0.141 | 7.62E-08 | 7.73E-06 | 4.03E-05 | 5.90E-04 | 0.131 |
| ETP-fw ⁴⁵ | CTUe | 22.2 | 23.9 | 0.0101 | 0.122 | 0.440 | 0.0984 | -1.64 |
| HTP-c ⁴⁵ | CTUh | 1.53E-09 | 1.63E-09 | 1.69E-13 | 2.06E-12 | 1.97E-11 | 1.17E-11 | -2.34E-09 |
| HTP-nc ⁴⁵ | CTUh | 2.73E-07 | 2.83E-07 | 1.06E-11 | 8.18E-11 | 6.56E-10 | 1.17E-09 | -7.68E-08 |
| SQP ⁴⁵ | dimensionless | 5.14 | 9.60 | 9.22E-05 | 8.58E-04 | 0.295 | 0.0258 | 0.682 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 9.05 | 10.8 | 1.31E-04 | 0.00149 | 0.496 | 0.0271 | 3.42 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 9.05 | 10.8 | 1.31E-04 | 0.00149 | 0.496 | 0.0271 | 3.42 |
| PENRE | MJ | 143 | 150 | 0.0401 | 0.304 | 2.30 | 0.332 | -50.6 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 143 | 150 | 0.0401 | 0.304 | 2.30 | 0.332 | -50.6 |
| SM | kg | 0.910 | 0.927 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0258 | 0.0277 | 3.38E-07 | 2.90E-06 | 0.00117 | 4.67E-05 | -0.0243 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 4.03E-09 | 1.33E-08 | 4.35E-14 | 4.94E-13 | 7.70E-11 | 5.01E-11 | -3.87E-10 |
| NHWD | kg | 0.256 | 0.271 | 5.73E-07 | 7.38E-06 | 7.19E-04 | 0.485 | 0.906 |
| RWD | kg | 7.59E-04 | 7.85E-04 | 5.88E-10 | 5.94E-08 | 3.14E-07 | 4.00E-06 | 9.91E-06 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 1.99 | 2.03 | 0 | 0 | 4.36 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 4.36 |
| Steel collected with mixed construction waste | kg | 0.484 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 4.36 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.484 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0422 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.60mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 14.1 | 14.6 | 0.00298 | 0.0226 | 0.210 | 0.0222 | -5.31 |
| ODP | kg CFC11-eq. | 8.32E-12 | 9.55E-12 | 2.83E-16 | 2.71E-15 | 1.12E-12 | 3.62E-14 | 1.00E-13 |
| AP | kg SO ₂ -eq. | 0.0406 | 0.0424 | 9.99E-06 | 4.17E-05 | 8.76E-04 | 5.93E-05 | -0.00509 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00391 | 0.00414 | 2.33E-06 | 9.06E-06 | 7.90E-05 | 6.32E-06 | -1.41E-04 |
| POCP | kg ethene-eq. | 0.00617 | 0.00637 | 9.85E-07 | -1.11E-05 | 4.69E-05 | 5.53E-06 | -0.00240 |
| ADPE | kg Sb-eq. | 3.47E-05 | 3.54E-05 | 3.69E-11 | 4.14E-10 | 1.79E-08 | 1.66E-09 | -2.72E-07 |
| ADPF | MJ | 140 | 147 | 0.0401 | 0.304 | 2.29 | 0.320 | -52.0 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.59E-10 | 2.79E-10 | 4.58E-15 | 6.32E-14 | 7.63E-12 | 1.02E-12 | 9.82E-11 |
| HTnc - GS | CTUh | 8.24E-11 | 4.48E-10 | 2.19E-15 | 1.42E-14 | 2.43E-13 | 2.37E-14 | 2.73E-12 |
| LU - GS | kg C deficit-eq. | 1.54 | 1.81 | 7.61E-06 | 5.89E-05 | 0.0239 | 0.00225 | 0.285 |
| RDW - GS | m ³ -eq. | 0.0120 | 0.0130 | 2.18E-07 | 1.84E-06 | 7.78E-04 | 2.35E-05 | -0.0132 |
| IR - GS | kBq U235-eq. | 0.137 | 0.141 | 7.62E-08 | 7.73E-06 | 4.03E-05 | 5.90E-04 | 0.131 |
| PM - GS | kg PM2.5-eq. | 0.00338 | 0.00351 | 7.17E-07 | 1.95E-06 | 5.74E-05 | 4.17E-06 | -4.00E-04 |

45. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

46. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

47. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.70mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 5.63 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 16.6 | 17.2 | 0.00351 | 0.0267 | 0.248 | 0.0273 | -6.51 |
| GWP-fossil | kg CO ₂ -eq. | 16.6 | 17.3 | 0.00351 | 0.0267 | 0.248 | 0.0272 | -6.51 |
| GWP-biogenic | kg CO ₂ -eq. | 2.10E-04 | -0.145 | 3.48E-07 | 8.89E-06 | 2.77E-04 | 5.37E-05 | 0.00378 |
| GWP-luluc | kg CO ₂ -eq. | 5.03E-04 | 0.00118 | 2.55E-08 | 2.87E-07 | 9.50E-06 | 1.64E-05 | -1.34E-04 |
| ODP | kg CFC-11-eq. | 7.74E-12 | 8.88E-12 | 2.79E-16 | 2.68E-15 | 1.10E-12 | 3.58E-14 | 9.97E-14 |
| AP | mol H ⁺ -eq. | 0.0570 | 0.0596 | 1.67E-05 | 6.88E-05 | 0.00125 | 8.58E-05 | -0.00651 |
| EP-freshwater | kg P-eq. | 3.30E-06 | 5.07E-06 | 6.17E-10 | 4.39E-09 | 1.35E-07 | 2.09E-08 | -1.16E-06 |
| EP-marine | kg N-eq. | 0.0124 | 0.0130 | 8.07E-06 | 3.11E-05 | 2.67E-04 | 2.09E-05 | -4.98E-04 |
| EP-terrestrial | mol N-eq. | 0.139 | 0.146 | 8.84E-05 | 3.42E-04 | 0.00291 | 2.29E-04 | 1.13E-04 |
| POCP | kg NMVOC-eq. | 0.0416 | 0.0436 | 2.26E-05 | 6.64E-05 | 7.40E-04 | 6.61E-05 | -0.00462 |
| ADP-minerals & metals ⁴⁸ | kg Sb-eq. | 3.48E-05 | 3.55E-05 | 4.29E-11 | 4.80E-10 | 2.08E-08 | 1.89E-09 | -3.28E-07 |
| ADP-fossil ⁴⁸ | MJ | 162 | 170 | 0.0466 | 0.354 | 2.68 | 0.385 | -59.0 |
| WDP ⁴⁸ | m ³ world-eq. deprived | 1.11 | 1.21 | 2.61E-05 | 1.69E-04 | 0.0968 | 0.00184 | -1.25 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁴⁹ | kg CO ₂ -eq. | 16.2 | 16.9 | 0.00348 | 0.0264 | 0.246 | 0.0264 | -6.27 |
| PM | Disease incidence | 7.39E-07 | 7.69E-07 | 1.89E-10 | 4.51E-10 | 1.21E-08 | 9.17E-10 | -7.30E-08 |
| IRP ⁵⁰ | kBq U-235-eq. | 0.140 | 0.144 | 8.85E-08 | 8.98E-06 | 4.68E-05 | 6.86E-04 | 0.153 |
| ETP-fw ⁴⁸ | CTUe | 24.6 | 26.7 | 0.0117 | 0.142 | 0.511 | 0.114 | -1.93 |
| HTP-c ⁴⁸ | CTUh | 1.69E-09 | 1.80E-09 | 1.97E-13 | 2.40E-12 | 2.29E-11 | 1.36E-11 | -2.73E-09 |
| HTP-nc ⁴⁸ | CTUh | 3.15E-07 | 3.26E-07 | 1.23E-11 | 9.50E-11 | 7.63E-10 | 1.37E-09 | -8.95E-08 |
| SQP ⁴⁸ | dimensionless | 5.63 | 10.8 | 1.07E-04 | 9.98E-04 | 0.342 | 0.0300 | 0.794 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 9.56 | 11.6 | 1.52E-04 | 0.00173 | 0.576 | 0.0315 | 3.99 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 9.56 | 11.6 | 1.52E-04 | 0.00173 | 0.576 | 0.0315 | 3.99 |
| PENRE | MJ | 162 | 170 | 0.0466 | 0.354 | 2.68 | 0.386 | -59.0 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 162 | 170 | 0.0466 | 0.354 | 2.68 | 0.386 | -59.0 |
| SM | kg | 1.06 | 1.08 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0274 | 0.0296 | 3.93E-07 | 3.37E-06 | 0.00136 | 5.43E-05 | -0.0283 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 4.38E-09 | 1.52E-08 | 5.06E-14 | 5.74E-13 | 8.94E-11 | 5.82E-11 | -4.52E-10 |
| NHWD | kg | 0.264 | 0.280 | 6.66E-07 | 8.58E-06 | 8.35E-04 | 0.564 | 1.04 |
| RWD | kg | 7.77E-04 | 8.06E-04 | 6.84E-10 | 6.91E-08 | 3.65E-07 | 4.65E-06 | 1.14E-05 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 2.32 | 2.36 | 0 | 0 | 5.06 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 5.06 |
| Steel collected with mixed construction waste | kg | 0.563 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 5.06 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.563 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0487 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.70mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 16.1 | 16.7 | 0.00346 | 0.0263 | 0.244 | 0.0258 | -6.19 |
| ODP | kg CFC11-eq. | 9.14E-12 | 1.06E-11 | 3.29E-16 | 3.15E-15 | 1.30E-12 | 4.21E-14 | 1.15E-13 |
| AP | kg SO ₂ -eq. | 0.0460 | 0.0481 | 1.16E-05 | 4.84E-05 | 0.00102 | 6.89E-05 | -0.00596 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00445 | 0.00471 | 2.70E-06 | 1.05E-05 | 9.18E-05 | 7.34E-06 | -1.67E-04 |
| POCP | kg ethene-eq. | 0.00711 | 0.00733 | 1.15E-06 | -1.29E-05 | 5.45E-05 | 6.42E-06 | -0.00279 |
| ADPE | kg Sb-eq. | 3.48E-05 | 3.55E-05 | 4.29E-11 | 4.81E-10 | 2.08E-08 | 1.92E-09 | -3.17E-07 |
| ADPF | MJ | 159 | 167 | 0.0466 | 0.353 | 2.66 | 0.372 | -60.6 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.73E-10 | 2.96E-10 | 5.33E-15 | 7.34E-14 | 8.87E-12 | 1.19E-12 | 1.14E-10 |
| HTnc - GS | CTUh | 9.06E-11 | 5.15E-10 | 2.55E-15 | 1.65E-14 | 2.82E-13 | 2.76E-14 | 3.18E-12 |
| LU - GS | kg C deficit-eq. | 1.77 | 2.07 | 8.84E-06 | 6.84E-05 | 0.0278 | 0.00261 | 0.332 |
| RDW - GS | m ³ -eq. | 0.0129 | 0.0141 | 2.53E-07 | 2.14E-06 | 9.04E-04 | 2.73E-05 | -0.0154 |
| IR - GS | kBq U235-eq. | 0.140 | 0.144 | 8.85E-08 | 8.98E-06 | 4.68E-05 | 6.86E-04 | 0.153 |
| PM - GS | kg PM2.5-eq. | 0.00384 | 0.00399 | 8.33E-07 | 2.27E-06 | 6.68E-05 | 4.85E-06 | -4.69E-04 |

48. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

49. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

50. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.75mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 6.02 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 17.6 | 18.2 | 0.00376 | 0.0285 | 0.265 | 0.0292 | -6.97 |
| GWP-fossil | kg CO ₂ -eq. | 17.6 | 18.4 | 0.00376 | 0.0285 | 0.265 | 0.0291 | -6.97 |
| GWP-biogenic | kg CO ₂ -eq. | 5.22E-04 | -0.155 | 3.72E-07 | 9.51E-06 | 2.96E-04 | 5.74E-05 | 0.00404 |
| GWP-luluc | kg CO ₂ -eq. | 5.18E-04 | 0.00124 | 2.73E-08 | 3.07E-07 | 1.02E-05 | 1.75E-05 | -1.43E-04 |
| ODP | kg CFC-11-eq. | 8.09E-12 | 9.30E-12 | 2.99E-16 | 2.86E-15 | 1.18E-12 | 3.82E-14 | 1.06E-13 |
| AP | mol H ⁺ -eq. | 0.0603 | 0.0631 | 1.79E-05 | 7.36E-05 | 0.00133 | 9.18E-05 | -0.00698 |
| EP-freshwater | kg P-eq. | 3.44E-06 | 5.34E-06 | 6.60E-10 | 4.69E-09 | 1.45E-07 | 2.23E-08 | -1.25E-06 |
| EP-marine | kg N-eq. | 0.0131 | 0.0138 | 8.63E-06 | 3.33E-05 | 2.85E-04 | 2.24E-05 | -5.37E-04 |
| EP-terrestrial | mol N-eq. | 0.148 | 0.155 | 9.45E-05 | 3.66E-04 | 0.00312 | 2.45E-04 | 7.87E-05 |
| POCP | kg NMVOC-eq. | 0.0441 | 0.0463 | 2.42E-05 | 7.11E-05 | 7.92E-04 | 7.07E-05 | -0.00496 |
| ADP-minerals & metals ⁵¹ | kg Sb-eq. | 3.48E-05 | 3.55E-05 | 4.59E-11 | 5.14E-10 | 2.22E-08 | 2.03E-09 | -3.52E-07 |
| ADP-fossil ⁵¹ | MJ | 172 | 181 | 0.0499 | 0.378 | 2.86 | 0.412 | -63.2 |
| WDP ⁵¹ | m ³ world-eq. deprived | 1.15 | 1.26 | 2.79E-05 | 1.80E-04 | 0.104 | 0.00197 | -1.34 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁵² | kg CO ₂ -eq. | 17.2 | 18.0 | 0.00372 | 0.0283 | 0.263 | 0.0282 | -6.71 |
| PM | Disease incidence | 7.84E-07 | 8.16E-07 | 2.02E-10 | 4.82E-10 | 1.30E-08 | 9.81E-10 | -7.85E-08 |
| IRP ⁵³ | kBq U-235-eq. | 0.142 | 0.146 | 9.47E-08 | 9.61E-06 | 5.01E-05 | 7.34E-04 | 0.164 |
| ETP-fw ⁵¹ | CTUe | 25.9 | 28.0 | 0.0125 | 0.152 | 0.547 | 0.122 | -2.07 |
| HTP-c ⁵¹ | CTUh | 1.77E-09 | 1.89E-09 | 2.10E-13 | 2.56E-12 | 2.45E-11 | 1.45E-11 | -2.92E-09 |
| HTP-nc ⁵¹ | CTUh | 3.36E-07 | 3.48E-07 | 1.31E-11 | 1.02E-10 | 8.16E-10 | 1.46E-09 | -9.59E-08 |
| SQP ⁵¹ | dimensionless | 5.88 | 11.4 | 1.15E-04 | 0.00107 | 0.366 | 0.0320 | 0.849 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 9.82 | 12.0 | 1.63E-04 | 0.00185 | 0.616 | 0.0337 | 4.27 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 9.82 | 12.0 | 1.63E-04 | 0.00185 | 0.616 | 0.0337 | 4.27 |
| PENRE | MJ | 172 | 181 | 0.0499 | 0.378 | 2.86 | 0.413 | -63.2 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 172 | 181 | 0.0499 | 0.378 | 2.86 | 0.413 | -63.2 |
| SM | kg | 1.14 | 1.16 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0283 | 0.0305 | 4.20E-07 | 3.60E-06 | 0.00146 | 5.81E-05 | -0.0303 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 4.56E-09 | 1.61E-08 | 5.41E-14 | 6.14E-13 | 9.57E-11 | 6.23E-11 | -4.85E-10 |
| NHWD | kg | 0.267 | 0.285 | 7.13E-07 | 9.18E-06 | 8.94E-04 | 0.603 | 1.11 |
| RWD | kg | 7.87E-04 | 8.16E-04 | 7.31E-10 | 7.39E-08 | 3.90E-07 | 4.97E-06 | 1.22E-05 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 2.48 | 2.53 | 0 | 0 | 5.42 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 5.42 |
| Steel collected with mixed construction waste | kg | 0.602 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 5.42 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.602 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0520 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.75mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 17.1 | 17.7 | 0.00370 | 0.0281 | 0.261 | 0.0276 | -6.63 |
| ODP | kg CFC11-eq. | 9.55E-12 | 1.11E-11 | 3.51E-16 | 3.37E-15 | 1.39E-12 | 4.50E-14 | 1.22E-13 |
| AP | kg SO ₂ -eq. | 0.0487 | 0.0509 | 1.24E-05 | 5.18E-05 | 0.00109 | 7.37E-05 | -0.00639 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00472 | 0.00500 | 2.89E-06 | 1.13E-05 | 9.82E-05 | 7.86E-06 | -1.80E-04 |
| POCP | kg ethene-eq. | 0.00757 | 0.00781 | 1.22E-06 | -1.38E-05 | 5.83E-05 | 6.87E-06 | -0.00299 |
| ADPE | kg Sb-eq. | 3.48E-05 | 3.56E-05 | 4.59E-11 | 5.14E-10 | 2.22E-08 | 2.06E-09 | -3.40E-07 |
| ADPF | MJ | 169 | 177 | 0.0499 | 0.377 | 2.85 | 0.398 | -64.9 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 2.80E-10 | 3.04E-10 | 5.70E-15 | 7.85E-14 | 9.49E-12 | 1.27E-12 | 1.23E-10 |
| HTnc - GS | CTUh | 9.47E-11 | 5.49E-10 | 2.73E-15 | 1.77E-14 | 3.02E-13 | 2.95E-14 | 3.41E-12 |
| LU - GS | kg C deficit-eq. | 1.88 | 2.20 | 9.46E-06 | 7.32E-05 | 0.0298 | 0.00279 | 0.356 |
| RDW - GS | m ³ -eq. | 0.0134 | 0.0147 | 2.70E-07 | 2.29E-06 | 9.67E-04 | 2.92E-05 | -0.0165 |
| IR - GS | kBq U235-eq. | 0.142 | 0.146 | 9.47E-08 | 9.61E-06 | 5.01E-05 | 7.34E-04 | 0.164 |
| PM - GS | kg PM2.5-eq. | 0.00407 | 0.00423 | 8.91E-07 | 2.43E-06 | 7.14E-05 | 5.19E-06 | -5.04E-04 |

51. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

52. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

53. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 0.95mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 7.59 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 21.7 | 22.5 | 0.00474 | 0.0360 | 0.334 | 0.0368 | -8.82 |
| GWP-fossil | kg CO ₂ -eq. | 21.7 | 22.7 | 0.00474 | 0.0360 | 0.334 | 0.0367 | -8.83 |
| GWP-biogenic | kg CO ₂ -eq. | 0.00177 | -0.195 | 4.69E-07 | 1.20E-05 | 3.73E-04 | 7.24E-05 | 0.00509 |
| GWP-luluc | kg CO ₂ -eq. | 5.78E-04 | 0.00149 | 3.44E-08 | 3.87E-07 | 1.28E-05 | 2.21E-05 | -1.82E-04 |
| ODP | kg CFC-11-eq. | 9.48E-12 | 1.10E-11 | 3.76E-16 | 3.61E-15 | 1.49E-12 | 4.82E-14 | 1.32E-13 |
| AP | mol H ⁺ -eq. | 0.0738 | 0.0773 | 2.25E-05 | 9.28E-05 | 0.00168 | 1.16E-04 | -0.00889 |
| EP-freshwater | kg P-eq. | 4.04E-06 | 6.43E-06 | 8.33E-10 | 5.92E-09 | 1.83E-07 | 2.81E-08 | -1.58E-06 |
| EP-marine | kg N-eq. | 0.0161 | 0.0170 | 1.09E-05 | 4.19E-05 | 3.60E-04 | 2.82E-05 | -6.93E-04 |
| EP-terrestrial | mol N-eq. | 0.182 | 0.191 | 1.19E-04 | 4.61E-04 | 0.00393 | 3.09E-04 | -5.74E-05 |
| POCP | kg NMVOC-eq. | 0.0544 | 0.0572 | 3.05E-05 | 8.96E-05 | 9.98E-04 | 8.92E-05 | -0.00631 |
| ADP-minerals & metals ⁵⁴ | kg Sb-eq. | 3.50E-05 | 3.57E-05 | 5.79E-11 | 6.48E-10 | 2.80E-08 | 2.56E-09 | -4.45E-07 |
| ADP-fossil ⁵⁴ | MJ | 211 | 222 | 0.0629 | 0.477 | 3.61 | 0.520 | -80.0 |
| WDP ⁵⁴ | m ³ world-eq. deprived | 1.33 | 1.46 | 3.52E-05 | 2.28E-04 | 0.131 | 0.00249 | -1.69 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁵⁵ | kg CO ₂ -eq. | 21.2 | 22.2 | 0.00469 | 0.0356 | 0.331 | 0.0356 | -8.50 |
| PM | Disease incidence | 9.64E-07 | 1.00E-06 | 2.55E-10 | 6.08E-10 | 1.64E-08 | 1.24E-09 | -1.00E-07 |
| IRP ⁵⁶ | kBq U-235-eq. | 0.148 | 0.152 | 1.19E-07 | 1.21E-05 | 6.31E-05 | 9.25E-04 | 0.207 |
| ETP-fw ⁵⁴ | CTUe | 30.8 | 33.5 | 0.0158 | 0.191 | 0.689 | 0.154 | -2.64 |
| HTP-c ⁵⁴ | CTUh | 2.08E-09 | 2.23E-09 | 2.65E-13 | 3.23E-12 | 3.09E-11 | 1.83E-11 | -3.70E-09 |
| HTP-nc ⁵⁴ | CTUh | 4.19E-07 | 4.34E-07 | 1.66E-11 | 1.28E-10 | 1.03E-09 | 1.84E-09 | -1.21E-07 |
| SQP ⁵⁴ | dimensionless | 6.86 | 13.8 | 1.44E-04 | 0.00135 | 0.462 | 0.0404 | 1.07 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 10.9 | 13.6 | 2.06E-04 | 0.00233 | 0.777 | 0.0425 | 5.40 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 10.9 | 13.6 | 2.06E-04 | 0.00233 | 0.777 | 0.0425 | 5.40 |
| PENRE | MJ | 211 | 222 | 0.0629 | 0.477 | 3.61 | 0.520 | -80.0 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 211 | 222 | 0.0629 | 0.477 | 3.61 | 0.520 | -80.0 |
| SM | kg | 1.44 | 1.47 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0315 | 0.0343 | 5.30E-07 | 4.54E-06 | 0.00184 | 7.33E-05 | -0.0383 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 5.25E-09 | 1.98E-08 | 6.82E-14 | 7.74E-13 | 1.21E-10 | 7.85E-11 | -6.17E-10 |
| NHWD | kg | 0.282 | 0.303 | 8.99E-07 | 1.16E-05 | 0.00113 | 0.760 | 1.38 |
| RWD | kg | 8.23E-04 | 8.57E-04 | 9.22E-10 | 9.32E-08 | 4.92E-07 | 6.27E-06 | 1.52E-05 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 3.14 | 3.20 | 0 | 0 | 6.83 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 6.83 |
| Steel collected with mixed construction waste | kg | 0.759 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 6.83 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.759 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0650 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 0.95mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 21.1 | 21.8 | 0.00467 | 0.0355 | 0.329 | 0.0348 | -8.39 |
| ODP | kg CFC11-eq. | 1.12E-11 | 1.31E-11 | 4.43E-16 | 4.25E-15 | 1.75E-12 | 5.68E-14 | 1.52E-13 |
| AP | kg SO ₂ -eq. | 0.0595 | 0.0623 | 1.57E-05 | 6.53E-05 | 0.00137 | 9.29E-05 | -0.00813 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00580 | 0.00615 | 3.64E-06 | 1.42E-05 | 1.24E-04 | 9.91E-06 | -2.33E-04 |
| POCP | kg ethene-eq. | 0.00944 | 0.00974 | 1.54E-06 | -1.73E-05 | 7.36E-05 | 8.66E-06 | -0.00379 |
| ADPE | kg Sb-eq. | 3.50E-05 | 3.57E-05 | 5.79E-11 | 6.49E-10 | 2.80E-08 | 2.60E-09 | -4.30E-07 |
| ADPF | MJ | 208 | 218 | 0.0629 | 0.476 | 3.59 | 0.502 | -82.2 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 3.07E-10 | 3.37E-10 | 7.19E-15 | 9.90E-14 | 1.20E-11 | 1.60E-12 | 1.55E-10 |
| HTnc - GS | CTUh | 1.11E-10 | 6.83E-10 | 3.44E-15 | 2.23E-14 | 3.81E-13 | 3.72E-14 | 4.31E-12 |
| LU - GS | kg C deficit-eq. | 2.32 | 2.73 | 1.19E-05 | 9.22E-05 | 0.0375 | 0.00352 | 0.450 |
| RDW - GS | m ³ -eq. | 0.0154 | 0.0169 | 3.41E-07 | 2.89E-06 | 0.00122 | 3.68E-05 | -0.0209 |
| IR - GS | kBq U235-eq. | 0.148 | 0.152 | 1.19E-07 | 1.21E-05 | 6.31E-05 | 9.25E-04 | 0.207 |
| PM - GS | kg PM2.5-eq. | 0.00500 | 0.00520 | 1.12E-06 | 3.06E-06 | 9.00E-05 | 6.54E-06 | -6.42E-04 |

54. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

55. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

56. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 1.00mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 7.98 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 22.8 | 23.5 | 0.00499 | 0.0378 | 0.352 | 0.0387 | -9.28 |
| GWP-fossil | kg CO ₂ -eq. | 22.8 | 23.7 | 0.00499 | 0.0378 | 0.351 | 0.0386 | -9.29 |
| GWP-biogenic | kg CO ₂ -eq. | 0.00209 | -0.204 | 4.93E-07 | 1.26E-05 | 3.92E-04 | 7.61E-05 | 0.00535 |
| GWP-luluc | kg CO ₂ -eq. | 5.93E-04 | 0.00155 | 3.62E-08 | 4.07E-07 | 1.35E-05 | 2.32E-05 | -1.92E-04 |
| ODP | kg CFC-11-eq. | 9.83E-12 | 1.14E-11 | 3.96E-16 | 3.80E-15 | 1.56E-12 | 5.07E-14 | 1.38E-13 |
| AP | mol H ⁺ -eq. | 0.0772 | 0.0808 | 2.37E-05 | 9.76E-05 | 0.00177 | 1.22E-04 | -0.00937 |
| EP-freshwater | kg P-eq. | 4.19E-06 | 6.70E-06 | 8.76E-10 | 6.22E-09 | 1.92E-07 | 2.96E-08 | -1.66E-06 |
| EP-marine | kg N-eq. | 0.0168 | 0.0178 | 1.14E-05 | 4.41E-05 | 3.78E-04 | 2.96E-05 | -7.33E-04 |
| EP-terrestrial | mol N-eq. | 0.190 | 0.200 | 1.25E-04 | 4.85E-04 | 0.00413 | 3.25E-04 | -9.15E-05 |
| POCP | kg NMVOC-eq. | 0.0570 | 0.0599 | 3.21E-05 | 9.42E-05 | 0.00105 | 9.38E-05 | -0.00665 |
| ADP-minerals & metals ⁵⁷ | kg Sb-eq. | 3.50E-05 | 3.58E-05 | 6.09E-11 | 6.81E-10 | 2.95E-08 | 2.69E-09 | -4.69E-07 |
| ADP-fossil ⁵⁷ | MJ | 221 | 232 | 0.0662 | 0.502 | 3.80 | 0.547 | -84.2 |
| WDP ⁵⁷ | m ³ world-eq. deprived | 1.38 | 1.51 | 3.70E-05 | 2.39E-04 | 0.137 | 0.00262 | -1.78 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁵⁸ | kg CO ₂ -eq. | 22.2 | 23.2 | 0.00493 | 0.0375 | 0.348 | 0.0374 | -8.94 |
| PM | Disease incidence | 1.01E-06 | 1.05E-06 | 2.68E-10 | 6.40E-10 | 1.72E-08 | 1.30E-09 | -1.06E-07 |
| IRP ⁵⁹ | kBq U-235-eq. | 0.149 | 0.154 | 1.26E-07 | 1.27E-05 | 6.64E-05 | 9.73E-04 | 0.218 |
| ETP-fw ⁵⁷ | CTUe | 32.1 | 34.9 | 0.0166 | 0.201 | 0.725 | 0.162 | -2.78 |
| HTP-c ⁵⁷ | CTUh | 2.16E-09 | 2.32E-09 | 2.79E-13 | 3.40E-12 | 3.25E-11 | 1.92E-11 | -3.90E-09 |
| HTP-nc ⁵⁷ | CTUh | 4.40E-07 | 4.55E-07 | 1.74E-11 | 1.35E-10 | 1.08E-09 | 1.94E-09 | -1.28E-07 |
| SQP ⁵⁷ | dimensionless | 710 | 14.4 | 1.52E-04 | 0.00142 | 0.486 | 0.0425 | 1.13 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 11.1 | 14.0 | 2.16E-04 | 0.00245 | 0.817 | 0.0447 | 5.68 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 11.1 | 14.0 | 2.16E-04 | 0.00245 | 0.817 | 0.0447 | 5.68 |
| PENRE | MJ | 221 | 232 | 0.0662 | 0.502 | 3.80 | 0.547 | -84.2 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 221 | 232 | 0.0662 | 0.502 | 3.80 | 0.547 | -84.2 |
| SM | kg | 1.52 | 1.54 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0323 | 0.0352 | 5.57E-07 | 4.78E-06 | 0.00193 | 7.70E-05 | -0.0403 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 5.43E-09 | 2.08E-08 | 7.18E-14 | 8.14E-13 | 1.27E-10 | 8.26E-11 | -6.50E-10 |
| NHWD | kg | 0.286 | 0.307 | 9.45E-07 | 1.22E-05 | 0.00118 | 0.799 | 1.44 |
| RWD | kg | 8.32E-04 | 8.67E-04 | 9.70E-10 | 9.80E-08 | 5.18E-07 | 6.59E-06 | 1.59E-05 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 3.31 | 3.37 | 0 | 0 | 7.18 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 718 |
| Steel collected with mixed construction waste | kg | 0.798 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 718 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.798 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0683 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 1.00mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 22.1 | 22.8 | 0.00491 | 0.0373 | 0.346 | 0.0366 | -8.83 |
| ODP | kg CFC11-eq. | 1.16E-11 | 1.36E-11 | 4.66E-16 | 4.47E-15 | 1.84E-12 | 5.97E-14 | 1.60E-13 |
| AP | kg SO ₂ -eq. | 0.0622 | 0.0651 | 1.65E-05 | 6.87E-05 | 0.00144 | 9.77E-05 | -0.00856 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00607 | 0.00644 | 3.83E-06 | 1.49E-05 | 1.30E-04 | 1.04E-05 | -2.46E-04 |
| POCP | kg ethene-eq. | 0.00990 | 0.0102 | 1.62E-06 | -1.82E-05 | 7.74E-05 | 9.11E-06 | -0.00399 |
| ADPE | kg Sb-eq. | 3.50E-05 | 3.58E-05 | 6.09E-11 | 6.82E-10 | 2.95E-08 | 2.73E-09 | -4.53E-07 |
| ADPF | MJ | 218 | 228 | 0.0662 | 0.500 | 3.78 | 0.528 | -86.5 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 3.14E-10 | 3.45E-10 | 7.56E-15 | 1.04E-13 | 1.26E-11 | 1.68E-12 | 1.63E-10 |
| HTnc - GS | CTUh | 1.15E-10 | 7.17E-10 | 3.61E-15 | 2.34E-14 | 4.01E-13 | 3.91E-14 | 4.54E-12 |
| LU - GS | kg C deficit-eq. | 2.43 | 2.86 | 1.25E-05 | 9.70E-05 | 0.0395 | 0.00370 | 0.474 |
| RDW - GS | m ³ -eq. | 0.0158 | 0.0175 | 3.59E-07 | 3.04E-06 | 0.00128 | 3.87E-05 | -0.0220 |
| IR - GS | kBq U235-eq. | 0.149 | 0.154 | 1.26E-07 | 1.27E-05 | 6.64E-05 | 9.73E-04 | 0.218 |
| PM - GS | kg PM2.5-eq. | 0.00523 | 0.00544 | 1.18E-06 | 3.22E-06 | 9.47E-05 | 6.88E-06 | -6.76E-04 |

57. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

58. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

59. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 1.15mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 9.16 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 25.9 | 26.7 | 0.00572 | 0.0434 | 0.404 | 0.0444 | -10.7 |
| GWP-fossil | kg CO ₂ -eq. | 25.8 | 27.0 | 0.00572 | 0.0434 | 0.403 | 0.0443 | -10.7 |
| GWP-biogenic | kg CO ₂ -eq. | 0.00302 | -0.234 | 5.66E-07 | 1.45E-05 | 4.50E-04 | 8.73E-05 | 0.00614 |
| GWP-luluc | kg CO ₂ -eq. | 6.38E-04 | 0.00174 | 4.15E-08 | 4.67E-07 | 1.55E-05 | 2.66E-05 | -2.21E-04 |
| ODP | kg CFC-11-eq. | 1.09E-11 | 1.27E-11 | 4.54E-16 | 4.36E-15 | 1.79E-12 | 5.82E-14 | 1.58E-13 |
| AP | mol H ⁺ -eq. | 0.0873 | 0.0914 | 2.72E-05 | 1.12E-04 | 0.00203 | 1.40E-04 | -0.0108 |
| EP-freshwater | kg P-eq. | 4.63E-06 | 7.51E-06 | 1.01E-09 | 7.14E-09 | 2.20E-07 | 3.39E-08 | -1.91E-06 |
| EP-marine | kg N-eq. | 0.0191 | 0.0202 | 1.31E-05 | 5.06E-05 | 4.34E-04 | 3.40E-05 | -8.50E-04 |
| EP-terrestrial | mol N-eq. | 0.215 | 0.227 | 1.44E-04 | 5.57E-04 | 0.00474 | 3.73E-04 | -1.94E-04 |
| POCP | kg NMVOC-eq. | 0.0647 | 0.0680 | 3.68E-05 | 1.08E-04 | 0.00120 | 1.08E-04 | -0.00767 |
| ADP-minerals & metals ⁶⁰ | kg Sb-eq. | 3.52E-05 | 3.59E-05 | 6.98E-11 | 7.82E-10 | 3.38E-08 | 3.08E-09 | -5.39E-07 |
| ADP-fossil ⁶⁰ | MJ | 250 | 263 | 0.0759 | 0.576 | 4.36 | 0.627 | -96.8 |
| WDP ⁶⁰ | m ³ world-eq. deprived | 1.51 | 1.66 | 4.25E-05 | 2.75E-04 | 0.158 | 0.00300 | -2.05 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁶¹ | kg CO ₂ -eq. | 25.2 | 26.3 | 0.00566 | 0.0430 | 0.400 | 0.0429 | -10.3 |
| PM | Disease incidence | 1.14E-06 | 1.19E-06 | 3.08E-10 | 7.34E-10 | 1.97E-08 | 1.49E-09 | -1.22E-07 |
| IRP ⁶² | kBq U-235-eq. | 0.154 | 0.159 | 1.44E-07 | 1.46E-05 | 7.62E-05 | 0.00112 | 0.251 |
| ETP-fw ⁶⁰ | CTUe | 35.8 | 39.0 | 0.0191 | 0.231 | 0.832 | 0.186 | -3.20 |
| HTP-c ⁶⁰ | CTUh | 2.40E-09 | 2.58E-09 | 3.20E-13 | 3.90E-12 | 3.73E-11 | 2.21E-11 | -4.48E-09 |
| HTP-nc ⁶⁰ | CTUh | 5.02E-07 | 5.20E-07 | 2.00E-11 | 1.55E-10 | 1.24E-09 | 2.22E-09 | -1.47E-07 |
| SQP ⁶⁰ | dimensionless | 7.84 | 16.2 | 1.74E-04 | 0.00162 | 0.557 | 0.0488 | 1.30 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 11.9 | 15.2 | 2.48E-04 | 0.00281 | 0.937 | 0.0512 | 6.53 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 11.9 | 15.2 | 2.48E-04 | 0.00281 | 0.937 | 0.0512 | 6.53 |
| PENRE | MJ | 250 | 263 | 0.0759 | 0.576 | 4.36 | 0.628 | -96.8 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 250 | 263 | 0.0759 | 0.576 | 4.36 | 0.628 | -96.8 |
| SM | kg | 1.74 | 1.78 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0348 | 0.0380 | 6.39E-07 | 5.48E-06 | 0.00222 | 8.84E-05 | -0.0464 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 5.95E-09 | 2.35E-08 | 8.24E-14 | 9.34E-13 | 1.46E-10 | 9.48E-11 | -7.48E-10 |
| NHWD | kg | 0.296 | 0.321 | 1.08E-06 | 1.40E-05 | 0.00136 | 0.917 | 1.64 |
| RWD | kg | 8.59E-04 | 8.97E-04 | 1.11E-09 | 1.12E-07 | 5.94E-07 | 7.56E-06 | 1.82E-05 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 3.80 | 3.87 | 0 | 0 | 8.24 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 8.24 |
| Steel collected with mixed construction waste | kg | 0.916 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 8.24 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.916 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0781 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 1.15mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 25.1 | 25.9 | 0.00564 | 0.0428 | 0.397 | 0.0420 | -10.2 |
| ODP | kg CFC11-eq. | 1.28E-11 | 1.51E-11 | 5.35E-16 | 5.13E-15 | 2.11E-12 | 6.85E-14 | 1.82E-13 |
| AP | kg SO ₂ -eq. | 0.0704 | 0.0737 | 1.89E-05 | 7.88E-05 | 0.00166 | 1.12E-04 | -0.00987 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00688 | 0.00730 | 4.40E-06 | 1.71E-05 | 1.49E-04 | 1.20E-05 | -2.85E-04 |
| POCP | kg ethene-eq. | 0.0113 | 0.0117 | 1.86E-06 | -2.09E-05 | 8.88E-05 | 1.05E-05 | -0.00458 |
| ADPE | kg Sb-eq. | 3.52E-05 | 3.59E-05 | 6.99E-11 | 7.83E-10 | 3.38E-08 | 3.13E-09 | -5.21E-07 |
| ADPF | MJ | 247 | 259 | 0.0759 | 0.574 | 4.34 | 0.606 | -99.4 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 3.35E-10 | 3.70E-10 | 8.67E-15 | 1.19E-13 | 1.44E-11 | 1.93E-12 | 1.87E-10 |
| HTnc - GS | CTUh | 1.28E-10 | 8.18E-10 | 4.15E-15 | 2.69E-14 | 4.60E-13 | 4.49E-14 | 5.21E-12 |
| LU - GS | kg C deficit-eq. | 2.76 | 3.26 | 1.44E-05 | 1.11E-04 | 0.0453 | 0.00425 | 0.544 |
| RDW - GS | m ³ -eq. | 0.0173 | 0.0192 | 4.12E-07 | 3.49E-06 | 0.00147 | 4.44E-05 | -0.0253 |
| IR - GS | kBq U235-eq. | 0.154 | 0.159 | 1.44E-07 | 1.46E-05 | 7.62E-05 | 0.00112 | 0.251 |
| PM - GS | kg PM2.5-eq. | 0.00592 | 0.00617 | 1.36E-06 | 3.69E-06 | 1.09E-04 | 7.89E-06 | -7.80E-04 |

60. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

61. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

62. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Environmental Product Declaration

ZINCALUME® steel

Results for 1 m² of ZINCALUME® steel in 1.20mm base material thickness (BMT)

In accordance to EN 15804:2012+A2:2019

Product mass: 9.55 kg/m² flat

Note: Results for 'A1-A3 incl. rollforming' are for one square metre (1 m²) of flat product. The profile of the rollformed product will affect how many flat square metres are required to cover a given surface area.

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-------------------------------------|-----------------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-total | kg CO ₂ -eq. | 26.9 | 27.8 | 0.00597 | 0.0453 | 0.421 | 0.0463 | -11.1 |
| GWP-fossil | kg CO ₂ -eq. | 26.9 | 28.0 | 0.00597 | 0.0453 | 0.420 | 0.0462 | -11.1 |
| GWP-biogenic | kg CO ₂ -eq. | 0.00334 | -0.244 | 5.91E-07 | 1.51E-05 | 4.70E-04 | 9.11E-05 | 0.00641 |
| GWP-luluc | kg CO ₂ -eq. | 6.53E-04 | 0.00180 | 4.33E-08 | 4.87E-07 | 1.61E-05 | 2.78E-05 | -2.31E-04 |
| ODP | kg CFC-11-eq. | 1.12E-11 | 1.31E-11 | 4.74E-16 | 4.54E-15 | 1.87E-12 | 6.07E-14 | 1.64E-13 |
| AP | mol H ⁺ -eq. | 0.0907 | 0.0950 | 2.83E-05 | 1.17E-04 | 0.00211 | 1.46E-04 | -0.0113 |
| EP-freshwater | kg P-eq. | 4.78E-06 | 7.78E-06 | 1.05E-09 | 7.45E-09 | 2.30E-07 | 3.54E-08 | -1.99E-06 |
| EP-marine | kg N-eq. | 0.0198 | 0.0210 | 1.37E-05 | 5.28E-05 | 4.53E-04 | 3.55E-05 | -8.89E-04 |
| EP-terrestrial | mol N-eq. | 0.224 | 0.236 | 1.50E-04 | 5.81E-04 | 0.00494 | 3.89E-04 | -2.28E-04 |
| POCP | kg NMVOC-eq. | 0.0673 | 0.0707 | 3.84E-05 | 1.13E-04 | 0.00126 | 1.12E-04 | -0.00801 |
| ADP-minerals & metals ⁶³ | kg Sb-eq. | 3.52E-05 | 3.60E-05 | 7.28E-11 | 8.15E-10 | 3.53E-08 | 3.22E-09 | -5.62E-07 |
| ADP-fossil ⁶³ | MJ | 260 | 273 | 0.0792 | 0.600 | 4.54 | 0.654 | -101 |
| WDP ⁶³ | m ³ world-eq. deprived | 1.55 | 1.71 | 4.43E-05 | 2.86E-04 | 0.164 | 0.00313 | -2.14 |

Additional Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------------------|-------------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| GWP-GHG ⁶⁴ | kg CO ₂ -eq. | 26.2 | 27.4 | 0.00590 | 0.0448 | 0.417 | 0.0448 | -10.7 |
| PM | Disease incidence | 1.19E-06 | 1.24E-06 | 3.21E-10 | 7.65E-10 | 2.06E-08 | 1.56E-09 | -1.27E-07 |
| IRP ⁶⁵ | kBq U-235-eq. | 0.155 | 0.161 | 1.50E-07 | 1.52E-05 | 7.95E-05 | 0.00116 | 0.262 |
| ETP-fw ⁶³ | CTUe | 37.0 | 40.4 | 0.0199 | 0.241 | 0.868 | 0.194 | -3.35 |
| HTP-c ⁶³ | CTUh | 2.47E-09 | 2.66E-09 | 3.34E-13 | 4.07E-12 | 3.89E-11 | 2.30E-11 | -4.67E-09 |
| HTP-nc ⁶³ | CTUh | 5.23E-07 | 5.42E-07 | 2.08E-11 | 1.61E-10 | 1.29E-09 | 2.32E-09 | -1.53E-07 |
| SQP ⁶³ | dimensionless | 8.08 | 16.8 | 1.82E-04 | 0.00169 | 0.581 | 0.0509 | 1.35 |

Resource use

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|----------------|--------|-------------------------|----------|----------|---------|----------|---------|
| PERE | MJ | 12.1 | 15.6 | 2.59E-04 | 0.00293 | 0.977 | 0.0534 | 6.82 |
| PERM | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| PERT | MJ | 12.1 | 15.6 | 2.59E-04 | 0.00293 | 0.977 | 0.0534 | 6.82 |
| PENRE | MJ | 260 | 273 | 0.0792 | 0.600 | 4.54 | 0.655 | -101 |
| PENRM | MJ | 0.0447 | 0.0455 | 0 | 0 | 0 | 0 | 0 |
| PENRT | MJ | 260 | 273 | 0.0792 | 0.600 | 4.54 | 0.655 | -101 |
| SM | kg | 1.82 | 1.85 | 0 | 0 | 0 | 0 | 0 |
| RSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| NRSF | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| FW | m ³ | 0.0356 | 0.0390 | 6.67E-07 | 5.72E-06 | 0.00231 | 9.22E-05 | -0.0484 |

Waste Categories and Output Flows

| Parameter | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HWD | kg | 6.13E-09 | 2.45E-08 | 8.59E-14 | 9.74E-13 | 1.52E-10 | 9.89E-11 | -7.81E-10 |
| NHWD | kg | 0.300 | 0.326 | 1.13E-06 | 1.46E-05 | 0.00142 | 0.957 | 1.71 |
| RWD | kg | 8.68E-04 | 9.08E-04 | 1.16E-09 | 1.17E-07 | 6.20E-07 | 7.89E-06 | 1.89E-05 |
| CRU | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| MFR | kg | 3.96 | 4.04 | 0 | 0 | 8.60 | 0 | 0 |
| MER | kg | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EEE | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |
| EET | MJ | 0 | 0 | 0 | 0 | 0 | 0 | 0 |

End of Life

| Parameter | Unit | Total |
|---|------|-------|
| Steel collected separately | kg | 8.60 |
| Steel collected with mixed construction waste | kg | 0.955 |
| Recovery for re-use | kg | 0 |
| Recovery for recycling | kg | 8.60 |
| Recovery for energy recovery | kg | 0 |
| Disposal to landfill | kg | 0.955 |
| Assumptions for scenario | - | n/a |

Biogenic Carbon Content

| | Unit | A1-A3 | A1-A3 incl. rollforming |
|--------------------------------------|------|---------|-------------------------|
| Biogenic carbon content in product | kg C | 0 | 0 |
| Biogenic carbon content in packaging | kg C | 0.00183 | 0.0813 |

Note: 1 kg biogenic carbon is equivalent to 44/12 kg CO₂

Additional Results for 1 m² of ZINCALUME® steel in 1.20mm base metal thickness (BMT)

In accordance to EN 15804:2012+A1:2013

Environmental Impacts

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------------------------|----------|-------------------------|----------|-----------|----------|----------|-----------|
| GWP | kg CO ₂ -eq. | 26.1 | 27.0 | 0.00588 | 0.0447 | 0.414 | 0.0438 | -10.6 |
| ODP | kg CFC11-eq. | 1.32E-11 | 1.56E-11 | 5.58E-16 | 5.35E-15 | 2.20E-12 | 7.14E-14 | 1.89E-13 |
| AP | kg SO ₂ -eq. | 0.0731 | 0.0765 | 1.97E-05 | 8.22E-05 | 0.00173 | 1.17E-04 | -0.0103 |
| EP | kg PO ₄ ³⁻ -eq. | 0.00715 | 0.00758 | 4.59E-06 | 1.79E-05 | 1.56E-04 | 1.25E-05 | -2.99E-04 |
| POCP | kg ethene-eq. | 0.0118 | 0.0121 | 1.94E-06 | -2.18E-05 | 9.26E-05 | 1.09E-05 | -0.00478 |
| ADPE | kg Sb-eq. | 3.52E-05 | 3.60E-05 | 7.28E-11 | 8.16E-10 | 3.53E-08 | 3.27E-09 | -5.43E-07 |
| ADPF | MJ | 256 | 269 | 0.0792 | 0.599 | 4.52 | 0.632 | -104 |

Additional Green Star v1.3 Indicators

| Indicator | Unit | A1-A3 | A1-A3 incl. rollforming | C1 | C2 | C3 | C4 | D |
|-----------|---------------------|----------|-------------------------|----------|----------|----------|----------|-----------|
| HTc - GS | CTUh | 3.42E-10 | 3.78E-10 | 9.04E-15 | 1.25E-13 | 1.51E-11 | 2.01E-12 | 1.96E-10 |
| HTnc - GS | CTUh | 1.32E-10 | 8.52E-10 | 4.32E-15 | 2.80E-14 | 4.80E-13 | 4.68E-14 | 5.44E-12 |
| LU - GS | kg C deficit-eq. | 2.87 | 3.39 | 1.50E-05 | 1.16E-04 | 0.0472 | 0.00443 | 0.568 |
| RDW - GS | m ³ -eq. | 0.0178 | 0.0197 | 4.29E-07 | 3.64E-06 | 0.00154 | 4.63E-05 | -0.0264 |
| IR - GS | kBq U235-eq. | 0.155 | 0.161 | 1.50E-07 | 1.52E-05 | 7.94E-05 | 0.00116 | 0.262 |
| PM - GS | kg PM2.5-eq. | 0.00616 | 0.00641 | 1.41E-06 | 3.85E-06 | 1.13E-04 | 8.23E-06 | -8.14E-04 |

63. The results of this environmental impact indicator shall be used with care as the uncertainties on these results are high or as there is limited experience with the indicator.

64. This indicator includes all greenhouse gases included in GWP-total but excludes biogenic carbon dioxide emissions and uptake and biogenic carbon stored in the product as defined by the IPCC AR5 report (IPCC 2013). As this indicator uses the same characterisation factors as the GWP indicator required in v3.01 of the General Programme Instructions (GPI) of the International EPD® System, its inclusion creates comparability with EPDs based on other Product Category Rules (PCRs) aligned with v3.01 of the GPI, as well as comparability with other GHG reporting according ISO 14067.

65. This impact category deals mainly with the eventual impact of low dose ionizing radiation on human health of the nuclear fuel cycle. It does not consider effects due to possible nuclear accidents, occupational exposure nor due to radioactive waste disposal in underground facilities. Potential ionizing radiation from the soil, from radon and some construction materials, is also not measured by this indicator.

Interpretation of Results

Impact Category Results

The majority of production (A1-A3) impacts arise from the combustion of fossil fuels, either directly or in the upstream production of electricity and materials. The upstream production of Hot Rolled Coil steel substrate was the most significant contributor to most environmental impact indicators, and the base metal thickness (BMT) has significant influence on the results due to the dominance of the manufacturing of the steel substrate. This emphasises the importance of selecting the appropriate BMT for the intended application; where a thicker steel sheet does not contribute to structural integrity, a lighter-weight version of ZINCALUME® steel with a lower BMT should be considered.

The upstream production of metal coating alloys – a combination of aluminium, zinc and magnesium applied to the steel substrate for corrosion protection – was the most significant contributor to ADP-minerals & metals, IRP, and SQP, and also contributed significantly to most indicators.

Rollforming generally adds less than 5% to total impacts, but has significant impact for EP-freshwater, ODP, WDP, and SQP. These impacts were driven by the upstream production of electricity and cardboard used by rollformers.

Assumption of average product – Sensitivity of results

When similar products are manufactured on different production lines, there is sometimes variation in results. Should production scheduling change significantly, this may be reflected in changes in the calculated impacts. The reason for these differences is the different mix of production routes that contribute to each product. Where products are preferentially made at different locations, the differences are most evident. While unlikely, should production scheduling change significantly, this may be reflected in changes in the calculated impacts. The variation in impact across production lines for ZINCALUME® steel (flat product) is well under 10%.

References

AS 1397:2021, Continuous hot-dip metallic coated steel sheet and strip - Coatings of zinc and zinc alloyed with aluminium and magnesium.

EN 15804:2012+A1:2013, Sustainability of construction works – Environmental product declarations – Core rules for the product category of construction products

EN 15804:2012+A2:2019, Sustainability of construction works – Environmental product declarations – Core rules for the product category of construction products

General Programme Instructions for the International EPD® System, Version 3.01.

Instructions of the EPD Australasia Programme, Version 3.0.

ISO 14001:2015, Environmental management systems– Requirements with guidance for use

ISO 14021:2016, Environmental labels and declarations – Self-declared environmental claims (Type II environmental labelling)

ISO 14025:2006, Environmental labels and declarations – Type III environmental declarations – Principles and procedures

National Waste Report 2020, Pickin J et al., A report prepared for the Department of Agriculture, Water and the Environment by Blue Environment Pty Ltd, 4 November 2020, <https://www.dcceew.gov.au/environment/protection/waste/national-waste-reports/2020>

PCR 2012:01, Construction Products and Construction Services, Version 2.32, 2020.07.01

PCR 2019:14, Construction Products, Version 1.11, 2021-02-05

Sphera, GaBi LCA Database Documentation, 2020, <https://www.gabi-software.com/support/gabi/gabi-database-2022-lci-documentation>

For further reference

EPD Owner **BlueScope Steel Limited**
steeldirect@bluescopesteel.com

LCA Author **BlueScope Steel Limited**
steeldirect@bluescopesteel.com
thinkstep-anz.com
info@thinkstep-anz.com

Programme Operator **EPD Australasia Limited**
info@epd-australasia.com

Product Website steel.com.au

BlueScope Awards and Certificates (ISO 14001, Worldsteel Climate Action Programme) bluescope.com/sustainable-steel/awards-and-certificates/

ResponsibleSteel™ certification for Port Kembla Steelworks bluescope.com/sustainable-steel/responsiblesteel/

BlueScope Sustainability Reporting bluescope.com/sustainable-steel/reports/



For further information,
contact BlueScope Steel Direct

1800 800 789
steel.com.au

BlueScope Steel Limited

Level 11, 120 Collins St, Melbourne VIC 3000, Australia

ABN 16 000 011 058