

# REDCOR®

## weathering steel (plate) AS/NZS 3678 - WR350B, WR350LOB, WR350L20B

### General description

WR350B is a low phosphorous structural weathering steel with nominal yield strength of 340MPa for thicknesses from 10 to 80mm with options for guaranteed impact performance at 0 and -20°C.

### Typical uses

Heavy engineering structural elements such as bridges & bridge girders, towers, walls, heavy sculptures, frames, circular hollow section constructions, railway rolling stock.

### Features & benefits


Reduced atmospheric corrosion when used in the correct environments

Guaranteed minimum strength levels

Good toughness

Lower phosphorous levels for improved weldability

ACRS accreditation (ACRS Certificate No. 120802)

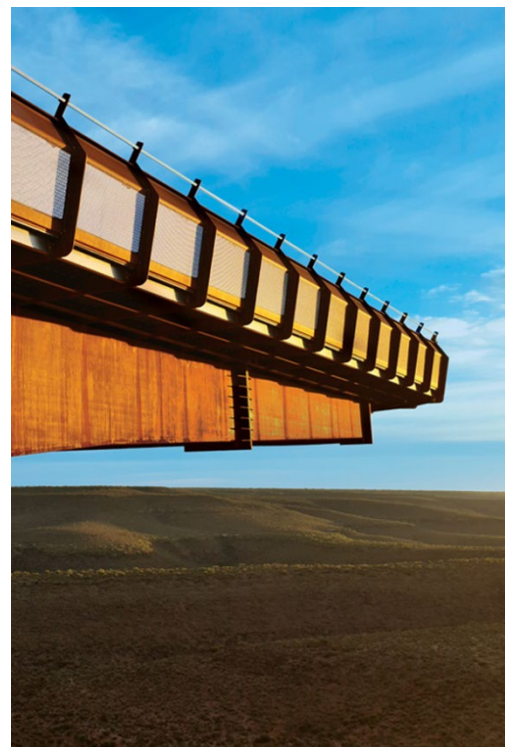

### Warnings

This material should be used in conjunction with the appropriate structural design and welding standards.

The weathering properties of this material is due to the formation of an impervious oxide layer through the use of alloy additions. Damage to this layer, or environmental conditions affecting the development of this layer, will impact on the effectiveness of the corrosion resistance.

Colour retention across welds can be achieved by appropriate electrode selection. Welds may be susceptible to hot cracking

Weathering steels are not recommended without further protection for buried or submerged situations or for applications exposed to concentrated industrial fumes or severe marine conditions.

Oxide staining of surrounding areas may occur due to run-off from this material.

Refer to BlueScope Technical Bulletin No. 26 for more information regarding the use of this material.

## Australian and International Standards

AS/NZS 3678:2016

AS/NZS 1365:1996 (R2016)

ISO 9001:2015 Quality System Certified

## Normal / optional supply conditions

	Normal	Optional
Thickness Range	10mm – 80mm	-
Length Range	By enquiry only	-
Availability	By enquiry only	-
Edge Condition	Trimmed	-
Tolerances	AS/NZS 1365:1996 (R2016)	-
Ultrasonic Inspection	-	AS 1710-2007 (R2017)
Surface Inspection	BlueScope	-
Certification	BlueScope	Third party endorsed

## Chemical composition

Element	Guaranteed Maximum %
Carbon	0.14
Silicon	0.75
Manganese	1.70
Phosphorus	0.04
Sulfur	0.030
Chromium	1.05
Nickel	0.55
Copper	0.50
Molybdenum	0.10
Aluminium	0.100*
Niobium**	0.025
Titanium	0.040
CEQ (IIW)	0.52

All values shown refer to the relevant Australian Standard unless otherwise stated

$$CEQ(IIW) = C + \frac{Mn}{6} + \frac{(Cr + Mo + V)}{5} + \frac{(Cu + Ni)}{15}$$

\* Values shown refer to the BlueScope internal standard

\*\* Niobium + Titanium + Vanadium  $\leq$  0.15%

## Mechanical properties

Tensile Properties (Transverse)		Thickness (mm)				
		9.95 < t ≤ 12	12 < t ≤ 20	20 < t ≤ 32	32 < t ≤ 50	50 < t ≤ 80
Yield Strength (MPa)	Guaranteed Min	340	340	340	340	340
Tensile Strength (MPa)	Guaranteed Min	450	450	450	450	450
Elongation 5.65√S <sub>0</sub> (%)	Guaranteed Min	20	20	20	20	20

Charpy Impact Properties	Longitudinal on 10 x 10mm test piece	Test Temperature (°C)	Absorbed Energy (joules)	
			Avg. of 3	Individual
Guaranteed minimum	WR350L0B	0	27	20
Guaranteed minimum	WR350L20B	-20	27	20

## Fire hazard properties

Test & Evaluation Method	Result
Combustibility test for materials (AS 1530.1-1994 (R2016))	Not deemed combustible (steel substrate) #

# These test results relate only to the behaviour of the test specimens of the material under the particular conditions of the test and they are not intended to be the sole criterion for assessing the potential fire hazard of the material in use.

RedCor®

[steel.com.au](http://steel.com.au)

To ensure you have the most current information

1800 024 402

[steeldirect@bluescopesteel.com](mailto:steeldirect@bluescopesteel.com)  
For more information contact Steel Direct



The information contained in this datasheet is provided by way of general information about this product only, and has not been prepared with your specific needs in mind. We recommend that you seek BlueScope's advice as to the suitability of this product for the purpose(s) for which you propose to use it. To contact BlueScope for advice about your proposed use of this product, please contact Steel Direct. REDCOR®, BlueScope and the BlueScope brand mark are registered trade marks of BlueScope Steel Limited. All rights reserved. © 2020 BlueScope Steel Limited ABN 16 000 011 058.